



Ion conducting and paramagnetic d-PCL(530)/siloxane-based biohybrids doped with Mn^{2+} ions

R.F.P. Pereira^{a,b,*}, J.P. Donoso^c, C.J. Magon^c, I.D.A. Silva^c, M.A. Cardoso^b,
M.C. Gonçalves^{b,d}, R.C. Sabadini^e, A. Pawlicka^e, V. de Zea Bermudez^{b,d}, M.M. Silva^{a,*}

^a Chemistry Centre and Chemistry Department, University of Minho, 4710-057 Braga, Portugal

^b Chemistry Department, University of Trás-os-Montes e Alto Douro, 5000-801 Vila Real, Portugal

^c IFSC, University of São Paulo, 13560-970 São Carlos, SP, Brazil

^d CQ-VR, University of Trás-os-Montes e Alto Douro, 5000-801 Vila Real, Portugal

^e IQSC, University of São Paulo, 13566-590 São Carlos, SP, Brazil

ARTICLE INFO

Article history:

Received 30 March 2016

Received in revised form 24 May 2016

Accepted 17 June 2016

Available online 18 June 2016

Keywords:

poly(ϵ -caprolactone)/siloxane biohybrids
manganese perchlorate
sol-gel
ionic conductivity
paramagnetism

ABSTRACT

Amorphous poly(ϵ -caprolactone) (PCL(530))/siloxane ormolytes doped with manganese perchlorate ($\text{Mn}(\text{ClO}_4)_2$) (d-PCL(530)/siloxane_n $\text{Mn}(\text{ClO}_4)_2$ with $n = 20, 50$, and 100), thermally stable up to at least 200°C , were synthesized by the sol-gel method. Ionic conductivity values up to 4.8×10^{-8} and $2.0 \times 10^{-6} \text{ S cm}^{-1}$ at about 25 and 100°C , respectively, were obtained for $n = 20$. FT-IR data demonstrated that the hydrogen bonding interactions present in the non-doped d-PCL(530)/siloxane host hybrid matrix were significantly influenced by the inclusion of $\text{Mn}(\text{ClO}_4)_2$ which promoted the formation of more oxyethylene/urethane and urethane/urethane aggregates. In addition, the Mn^{2+} ions bonded to all the “free” $\text{C}=\text{O}$ groups of the urethane cross-links and to some of the “free” ester groups of the amorphous PCL(530) chains. In the electrolytes, the ClO_4^- ions were found “free” and bonded to the Mn^{2+} ions along a bidentate configuration. The magnitude of the electron paramagnetic resonance (EPR) hyperfine constant of the analyzed samples ($A \approx 90 \times 10^{-4} \text{ cm}^{-1}$) suggested that the bonding between Mn^{2+} ions and the surrounding ligands is moderately ionic. The synthesized d-PCL(530)/siloxane_n $\text{Mn}(\text{ClO}_4)_2$ biohybrids have potential application in paramagnetic, photoelectrochemical and electrochromic devices.

© 2016 Elsevier Ltd. All rights reserved.

1. Introduction

Polymer electrolytes (PEs) have attracted much interest to the scientific community because of their technological application in the domain of solid state electrochemistry, in particular for the fabrication of advanced batteries, sensors, photoelectrochemical, and electrochromic devices (ECDs) [1–3]. Actual research on solid-state electrochemistry seeks a compromise between “green” technologies, low cost, and highly efficient materials.

In the framework of the investigation of new “green” materials with improved properties and potential application as electrolytes in ECDs, several ormolyte (organically modified silicate electrolyte) systems composed of a sol-gel derived [4] poly(ϵ -caprolactone) (PCL(530)), where 530 represents the average molecular weight in g

mol^{-1})-based di-urethanesil hybrid network (abbreviated as d-PCL(530)/siloxane) (Fig. 1) have been tested in the last few years. Doping of this organic-inorganic hybrid matrix with lithium [5–8], potassium [9], magnesium [10], europium [8], and erbium [6] salts, europium complexes [11] and ionic liquids [5] resulted in materials with attractive features, in particular high ionic conductivity and in the case of the lanthanide-containing systems also high luminescence, and foreseen applications in eco-friendly ECDs. Prior to these works, applications of PCL and PCL-based hybrids had been proposed almost exclusively for the biomedical field, as biodegradable suture, artificial skin, resorbable prostheses, containers for sustained drug delivery, or bioactive coatings [12–20]. In fact PCL is a linear biopolymer that possesses interesting features, such as biocompatibility, permeability, hydrophobicity, biodegradability, non-toxicity for living organisms, and the ability of being resorbed after a certain period of implantation time.

In the present work, the d-PCL(530)/siloxane biohybrid was doped with manganese perchlorate ($\text{Mn}(\text{ClO}_4)_2$). The incorporation of Mn^{2+} ions has a two-fold interest, endowing the resulting

* Corresponding authors.

E-mail addresses: rpereira@quimica.uminho.pt (R.F.P. Pereira), nini@quimica.uminho.pt (M.M. Silva).

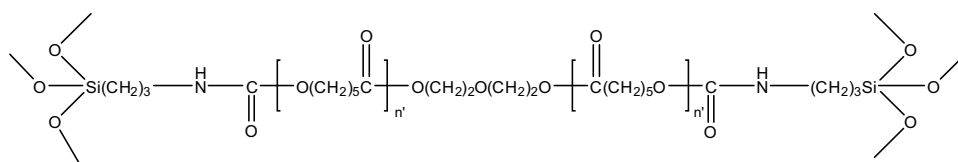


Fig. 1. Structure of the d-PCL(530)/siloxane hybrid host matrix with $2n' = 3.7$.

Table 1

Composition of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids.

n	m (PCL(530)) ± 0.01 (mg)	m (Mn(ClO ₄) ₂) ± 0.01 (mg)	n' (Mn(ClO ₄) ₂) (mmol)
100	803.83	14.25	0.056
50	805.14	28.54	0.112
20	806.72	71.48	0.282

hybrids with ionic conductivity and specially paramagnetic properties.

Indeed Mn²⁺ is a transition metal ion that has been extensively used as paramagnetic probe and as activator in various luminescent materials [21,22]. Mn²⁺-doped phosphors can be effectively excited by many sources, such as ultraviolet (UV), X-ray, and electric field [23–26] to yield emissions in the green, orange and red regions of the visible spectrum [21,27,28]. These emission properties motivated the wide use of Mn²⁺-based materials as phosphors for lamps and displays [25,27,29,30]. Recently, Wang et al. [31] proposed the use of carbon-coated manganese silicate to act as anode material for lithium storage, exhibiting outstanding rate performances and high-rate cycling stability, and meeting the requirement for fast charging/discharging Li⁺ batteries.

In this study, the structure, morphology, thermal features, ionic conductivity, and paramagnetic properties of the Mn(ClO₄)₂-doped d-PCL(530)/siloxane biohybrids are reported. The elucidation of the paramagnetic features has been performed by means of electron paramagnetic resonance spectroscopy (EPR), which is an effective and highly sensitive technique for the characterization of local order in a variety of solid-state systems [32–34]. EPR can provide valuable information about the oxidation state, ground state, and spin state of the paramagnetic ion. It enables the determination of the local symmetry of the ion environment, the nature of relevant spin interactions (e.g., Zeeman interaction, fine structure splitting, hyperfine coupling and exchange interaction) and the extent of covalency of the metal-ligand bond. EPR studies using Mn²⁺ ion as a probe have been very useful in the understanding of both the local coordination symmetry and magnetic properties of Mn²⁺ ions incorporated in a variety of materials, such as glasses [35–37], zeolites [38–40] and polymers [41].

We believe that the present investigation represents an important contribution towards the understanding of the interactions between the d-PCL(530)/siloxane systems and metal ions.

2. Experimental

2.1. Materials

Manganese (II) perchlorate (Mn(ClO₄)₂·xH₂O, 99%, Aldrich) was dried under vacuum at room temperature for several days prior to being used. α,ω-hydroxypoly(ε-caprolactone) (PCL (530), MW = 530 g mol⁻¹, Fluka) and 3-isocyanatepropyltriethoxysilane (ICPTES, 95%, Aldrich) were used as received. Ethanol (CH₃CH₂OH, 99.9%, Merck) and tetrahydrofuran (THF, 99.9%, Merck) were stored over molecular sieves. High-purity deionized water (H₂O) was used in all experiments.

2.2. Synthesis

The Mn(ClO₄)₂-doped d-PCL(530)/siloxane-based biohybrids were prepared based on the procedure described in detail elsewhere [7]. The first stage of the synthesis involved the formation of a urethane cross-link between the hydroxyl (–OH) end groups of the PCL(530) (0.8 g, 1.5 mmol) chains and the isocyanate (–N=C=O) groups of ICPTES (745 μL, 3.0 mmol) to yield the organic-inorganic hybrid precursor. This reaction occurred in THF medium at 70–80 °C and in a sealed flask. The grafting process was infrared monitored during the formation of the urethane groups. The intensity of the strong and sharp band, characteristic of the stretching vibration of the –N=C=O group of ICPTES and typically located at 2273 cm⁻¹, was progressively reduced until it disappeared upon completion of the reaction. In parallel, a series of new bands, associated with the vibrations of the urethane group, appeared in the 1800–1500 cm⁻¹ spectral region. The d-PCL(530)/siloxane precursor was obtained as a yellowish transparent oil.

In the second stage of the synthesis procedure, a mixture of CH₃CH₂OH (705 μL, 12.1 mmol) and H₂O (82 μL, 4.6 mmol) was added to the d-PCL(530)/siloxane precursor obtained in the previous step to promote the hydrolysis and condensation reactions characteristic of the sol-gel process. The molar ratio ICPTES:CH₃CH₂OH:H₂O used was 1:4:1.5. An appropriate mass of Mn(ClO₄)₂ (Table 1) was incorporated immediately after the addition of CH₃CH₂OH and H₂O. The final mixture was stirred for 30 min and then cast into a Teflon mould, which was covered with Parafilm and left in a fume cupboard for 24 h. Xerogel films were produced after aging for 1 month in an oven at 50 °C followed by drying under vacuum at 90 °C for 3 days prior to being analyzed.

The biohybrids prepared were produced as yellowish flexible xerogel films (Fig. 2) and were identified using the notation d-PCL



Fig. 2. Appearance of a representative d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrid.

(530)/siloxane_nMn(ClO₄)₂, where *n* (salt composition) indicates the number of (–C(=O)(CH₂)₅O–) PCL repeat units per Mn²⁺ ion. Samples with *n* = 100, 50 and 20 were prepared (Table 1).

2.3. Characterization

The total ionic conductivity of the samples was determined by locating an electrolyte disk between two 10 mm diameter ion-blocking gold electrodes (Goodfellow, >99.95%) to form a symmetrical cell. The electrode/ormolyte/electrode assembly was secured in a suitable constant volume support and installed in a Büchi TO51 tube oven with a K-type thermocouple (precision of about ±0.2 °C) placed close to the electrolyte disk to measure the sample temperature. Bulk conductivities of the electrolyte samples were obtained during heating cycles using the complex plane impedance technique with the Autolab PGSTAT-12 (Eco Chemie) equipment between room temperature (±20 °C) and 100 °C and at approximately 10 °C intervals. The ionic conductivity was evaluated for frequencies between 500 mHz and 65 kHz.

Differential scanning calorimetry (DSC) measurements were performed in a Mettler Toledo DSC 821e calorimeter. Prior to the analyses, the samples were dried in a desiccator containing phosphorous pentoxide (P₂O₅) for 3 days. The DSC analyses were conducted over a temperature range of 0 to 300 °C, at a heating rate of 10 °C min^{–1}, and under argon purge with 50 mL min^{–1} rate flow. All films were sealed in standard 40 μL aluminum crucibles (Mettler Toledo).

Thermogravimetric analysis (TGA) were performed with a Shimadzu TGA-50 equipment. The measurements were conducted between 30 and 900 °C, at a heating rate of 10 °C min^{–1}, and under a nitrogen atmosphere with 60 mL min^{–1} rate flow. Before each analysis and aiming to eliminate the traces of solvent and/or absorbed water, all the samples were subject to a first run from 30 to 105 °C, at a heating rate of 20 °C min^{–1}, followed by a second isothermal run at 105 °C during 10 minutes.

Polarized optical microscopy (POM) images were recorded using an OPTIKA B-600POL microscope equipped with a 8 Mpixel digital Photo Camera. The images were analyzed using the OPTIKA Vision Pro software.

X-ray diffraction (XRD) measurements were carried out at room temperature with X-ray Rigaku Utma 4 diffractometer, power of 50 kV/50 mA and Cu Kα irradiation, speed of 2 °C min^{–1}, in an angle range (2θ) of 3 to 60°, at room temperature.

Attenuated total reflectance Fourier transform infrared (ATR/FT-IR) spectra were registered in a Thermo Scientific Nicolet iS50 FTIR spectrometer, coupled to an ATR accessory with a diamond crystal. The instrument is controlled by the Omnic software package (version 9.2.28) from Thermo Fisher Scientific Inc. The spectra were collected in the 4000–400 cm^{–1} range by averaging 64 scans at a resolution of 4 cm^{–1}. To deconvolute complex band envelopes, the non-linear curve-fitting procedure offered by the PeakFit software [42] was employed. To automatically place hidden peaks, the Residuals procedure was used. This procedure initially places peaks by finding local maxima in a smoothed data stream. Hidden peaks are then optionally added where peaks in the residuals occur. The best fit of the experimental data was obtained using Gaussian shapes and by varying the frequency, bandwidth, and intensity of the bands. A linear baseline correction with a tolerance of 0.2 % was employed. The standard errors of the curve-fitting procedure were <0.03.

X-band continuous-wave electron paramagnetic resonance (CW-EPR) spectra were recorded at 50 K on a Bruker Elexsys E580 spectrometer operating at 9.478 GHz, equipped with a continuous flow liquid helium Oxford cryogenic system. Solid state powder EPR spectra were simulated by the function “pepper”

of the software package EasySpin [43] implemented in MATLAB (MathWorks, Inc.).

3. Results and Discussion

3.1. Thermal characterization

The DSC thermograms of the d-PCL(530)/siloxane₂₀Mn(ClO₄)₂ biohybrids (Fig. 3) confirm the entirely amorphous character of the doped samples indicating that the addition of the salt did not alter the disordered nature of the host hybrid matrix [7]. In the case of d-PCL(530)/siloxane₂₀Mn(ClO₄)₂ and d-PCL(530)/siloxane₅₀Mn(ClO₄)₂ a weak broad endothermic peak is seen at ca. 98 °C (onset at about 36 °C) and at ca. 91 °C (onset at about 14 °C), respectively. This endotherm probably corresponds to the loss of adsorbed solvent(s).

The DSC curve of the salt (Fig. 3) displays two endothermic peaks centred at ca. 50 °C (onset at ca. 46 °C) and 155 °C (onset at ca. 145 °C). While the former event corresponds to a phase transition, a phenomenon often encountered in perchlorate salts [44,45], the latter endotherm is associated with melting [46]. None of these two peaks is seen in the DSC curves of the doped d-PCL(530)/siloxane materials suggesting the complete dissociation of Mn(ClO₄)₂ in the d-PCL(530)/siloxane medium.

The thermal behavior of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids was also evaluated by TGA. The TGA curves shown in Fig. 4 demonstrate that below 200 °C all the xerogel samples are thermally stable. The onset of thermal degradation of the d-PCL(530)/siloxane_nMn(ClO₄)₂ materials is lower than that reported for the non-doped d-PCL(530)/siloxane network (around 300 °C) [9] indicating that the presence of this guest salt had a non-stabilizing influence on the host d-PCL(530)/siloxane framework under an inert atmosphere. However, this value is similar to that found earlier for d-PCL(530)/siloxane-based ormolytes doped with a mixture of LiCF₃SO₃ and Er(CF₃SO₃)₃ [6]. Between 200 and 300 °C all the samples suffered an abrupt weight loss. At 300 °C the d-PCL(530)/siloxane₂₀Mn(ClO₄)₂ hybrid revealed a dramatic weight loss of about 25%. Interestingly, the marked weight loss of this salt-rich sample is similar to that observed in the case of the Mn(ClO₄)₂ TGA curve. In the 300–500 °C temperature range the thermal decomposition of all the doped samples was a multistep process (Fig. S1). Between 500 and 900 °C, a plateau was attained and no further thermal degradation occurred. At the maximum temperature

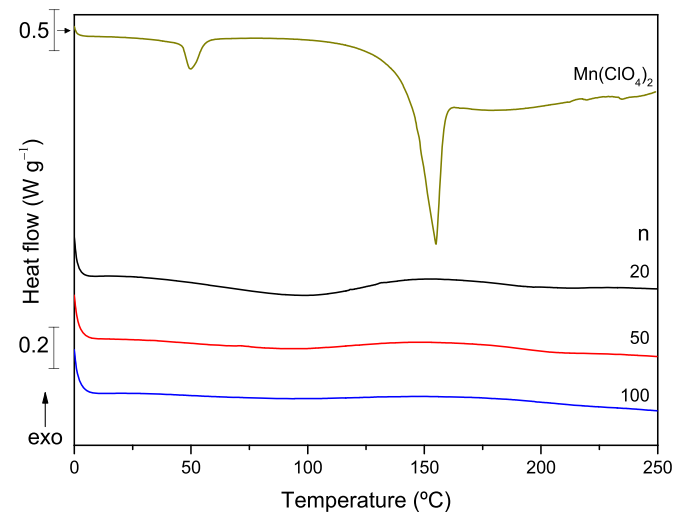


Fig. 3. DSC thermograms of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids and of the Mn(ClO₄)₂ salt.

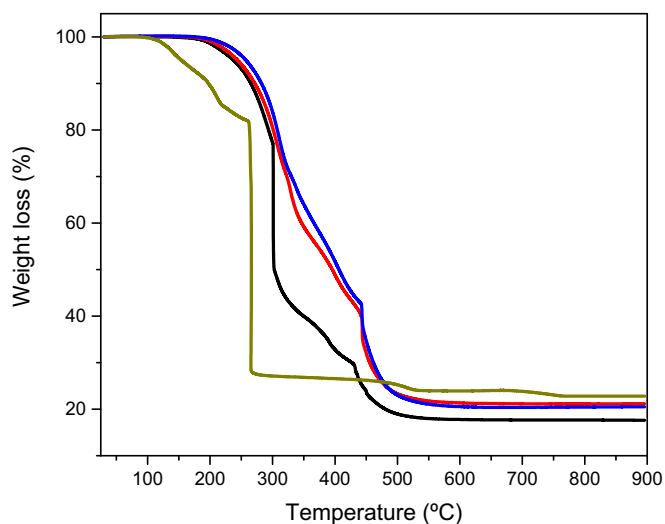


Fig. 4. TGA curves of the d-PLC(530)/siloxane_nMn(ClO₄)₂ biohybrids with $n = 100$ (blue line), $n = 50$ (red line), $n = 20$ (black line) and $n = 0$ (dark yellow line). (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

analyzed about 20% of the xerogels with $n = 100$, 50 and 20 still remained to be decomposed. In summary, the progressive incorporation of Mn(ClO₄)₂ into d-PCL(530)/siloxane had a gradual negative impact on the thermal stability of the host framework. However, the thermal decomposition onset value is considered adequate for solid-state electrochemical devices.

3.2. XRD and POM analyses

The XRD patterns of d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids display a broad peak, Gaussian in shape and centered at ca. 21° (Fig. 5a). This peak, which is associated with ordering of the siliceous domains [47] reveals that the incorporation of the manganese salt did not affect the amorphous character of the non-doped d-PCL(530)/siloxane matrix [7,9]. The POM images of the biohybrids (Fig. 5b) demonstrate the isotropic character of the samples, corroborating the XRD and DSC.

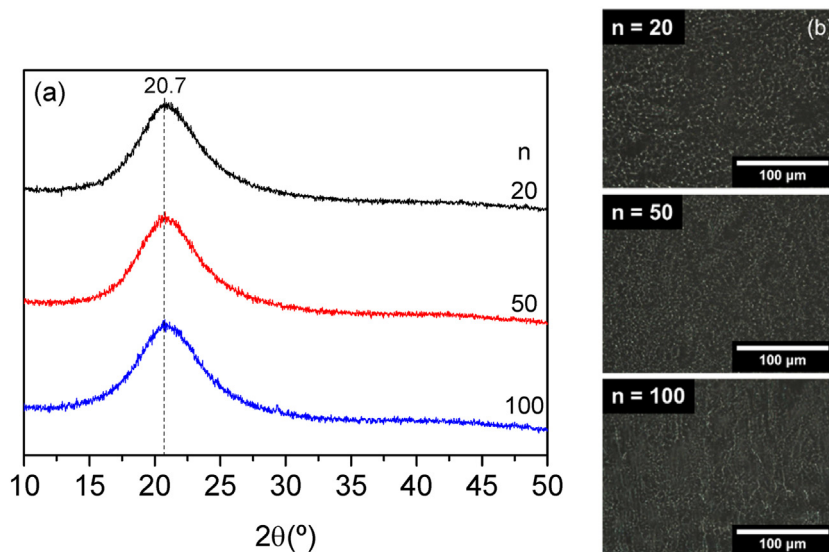


Fig. 5. (a) XRD patterns and (b) POM images of the d-PLC(530)/siloxane_nMn(ClO₄)₂ biohybrids with $n = 100$ (blue line), $n = 50$ (red line) and $n = 20$ (black line). (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

3.3. Ionic conductivity

AC Impedance spectroscopy was employed to evaluate the electrochemical properties of the biohybrids. The results are presented through Nyquist plots (imaginary impedance Z'' versus real impedance Z') (Fig. 6) and a plot of the temperature dependence of the ionic conductivity (Fig. 7).

The ionic conductivity was measured during the heating cycles and determined by Eq. (1),

$$\sigma = \frac{d}{A \times R_b} \quad (1)$$

where d is the thickness, A is the electrochemical active area and R_b is the bulk resistance obtained from the intercept of the imaginary impedance (minimum value of Z'') with the slanted line in the real impedance (Z') through the Randles circuit [48]. The Nyquist plots of Fig. 6 illustrate the mobility of ions due to charge transfer and diffusion processes. The Nyquist impedance plot can be used to determine the appropriate equivalent circuit and to estimate the values of the circuit parameters which reflect the carrier transport properties and the reaction in the electrode interface [49,50]. Typically, the Nyquist plot is described by three distinct parts: a semicircle located at the high-frequency range that corresponds to the charge transfer process, a straight line for lower frequencies that is related to the diffusion process, and the transition between these phenomena [2,3]. The AC responses, represented in Fig. 6 as Nyquist plots, show an inclined straight-line (typical of the blocking electrode capacitive behavior) whose intercept with the real axes, Z' , gives the PCL(530)/siloxane-based electrolyte membrane ionic resistance [2,51]. This value was obtained through analysis of the impedance responses, performed using a common approach, i.e., by defining an equivalent circuit taking into account all possible contributions to the impedance of the tested membranes [2,51]. The validity of the chosen circuit was confirmed by fitting the impedance responses using a Non-Linear Least-Square (NLLSQ) fit software developed by Boukamp [52,53].

In the three cases reproduced in Fig. 6 the semi-circle at higher frequencies disappears gradually with increasing salt concentration and increasing temperatures. The decreased bulk resistance indicates that the salt facilitates the charge transfer process due to the increase of ionic conductivity with respect to the non-doped

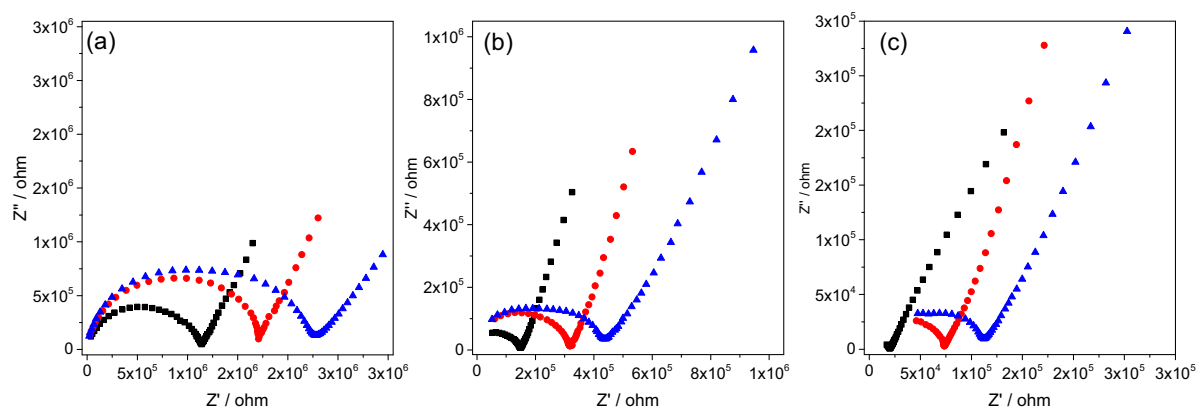


Fig. 6. Nyquist plots of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids with $n = 100$ (blue symbols), $n = 50$ (red symbols) and $n = 20$ (black symbols), at 25 °C (a), 50 °C (b), and 105 °C (c). (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

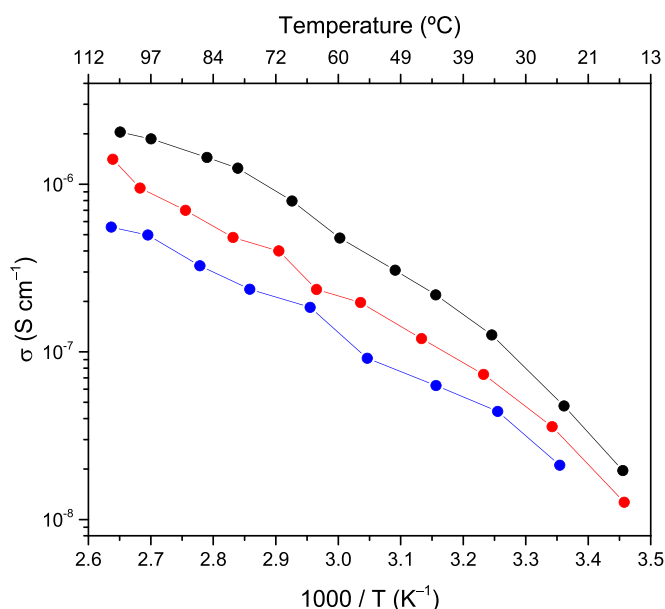


Fig. 7. Conductivity plot of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids for $n = 100$ (blue symbols), $n = 50$ (red symbols) and $n = 20$ (black symbols). The lines are just guides for the eyes. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

matrix [10]. The decrease of the semi-circles diameter also suggests that the ion diffusion ability is improved with salt content. Fig. 6 shows that salt content influences moderately the diffusion process. The straight line for lower frequencies does not change significantly with increasing salt content due to the migration of charges and the surface in-homogeneity of the electrodes [54]. Accordingly, the analysis of Fig. 7 allows inferring that the progressive addition of salt to d-PCL(530)/siloxane induced the enhancement of the ionic conductivity. The highest values were measured at $n = 20$ (4.8×10^{-8} and 2.0×10^{-6} S cm⁻¹ at about 25 and 100 °C, respectively).

The temperature dependence of the ionic conductivity of the hybrid samples, displayed in Fig. 7, appears to follow a free-volume model, i.e., Vogel-Tammann-Fulcher (VTF) type profile in the measured temperature range.

As the temperature increases, the polymer segments has acquired sufficient energy to push against the hydrostatic pressure imposed by its neighboring ions and thus polymer can expand easily to produce free volume. The free volume around the polymer chains determines the resulting conductivity, represented by the

overall mobility of ions and the polymer. Therefore, as temperature increases, ions or polymer segments can move into the free volume [55]. The ionic conductivity values exhibited by the ormolytes prepared in this work indicate that they are suitable for application on photoelectrochemical and electrochromic devices [56,57]. The levels of ionic conductivity are also of the same order of magnitude as those reported for analogous hybrids doped with potassium [9] and magnesium [10] triflates, and approximately one order of magnitude lower than those measured for analogues doped with lithium [7–10,58,59] or copper [7–10,58,59] salts.

3.4. FT-IR analysis

In the d-PCL(530)/siloxane hybrid medium the Mn²⁺ ions may coordinate to the available functional groups provided by the host hybrid framework (the ether —C—O—C— oxygen atoms and the ester C=O oxygen atoms of the PCL chains, and the urethane C=O oxygen atoms of the cross-links) or naturally to the counter-ions (i.e., the perchlorate ions) [60]. Given the minor amount of ether groups per PCL(530) repeat unit, it is clear that the C=O oxygen atoms will essentially be the main responsible for Mn²⁺ coordination. Therefore, upon incorporation into the host hybrid, these cations will bound to “free” urethane/ester C=O groups or to C=O groups present in hydrogen-bonded aggregates. In the latter case, the Mn²⁺ ions need to destroy hydrogen bonds of these aggregates, leading to their partial or complete destruction. To evaluate the influence of Mn²⁺ doping on the strength and extent of the hydrogen bonding interactions in the d-PCL(530)/siloxane matrix, we carried out an FT-IR spectroscopic analysis of the samples in the 1800–1600 cm⁻¹ spectral interval, usually known as amide I band. This band can be resolved into several individual components corresponding to different C=O environments: from “free” C=O groups (in the high-frequency range) to hydrogen-bonded aggregates of variable strength (in the mid-to-low-frequency range).

The FT-IR spectrum of the non-doped d-PCL(530)/siloxane matrix exhibits four components situated at 1762, 1736, 1720, and 1692 cm⁻¹ [11]. Each of these bands are associated with different C=O chemical environments: the 1762 cm⁻¹ and 1736 cm⁻¹ bands are attributed to “free” C=O groups of the urethane cross-links (A1) and of the ester groups of amorphous PCL(530) chains (A2), respectively; the 1720 cm⁻¹ band indicates the presence of oxyethylene/urethane hydrogen-bonded aggregates (B1); whereas the components around 1692 and 1670 cm⁻¹ are assigned to the absorption of C=O groups belonging to significantly more ordered hydrogen-bonded urethane/urethane (C1) and ester/urethane (C2) aggregates [11,61–63], respectively.

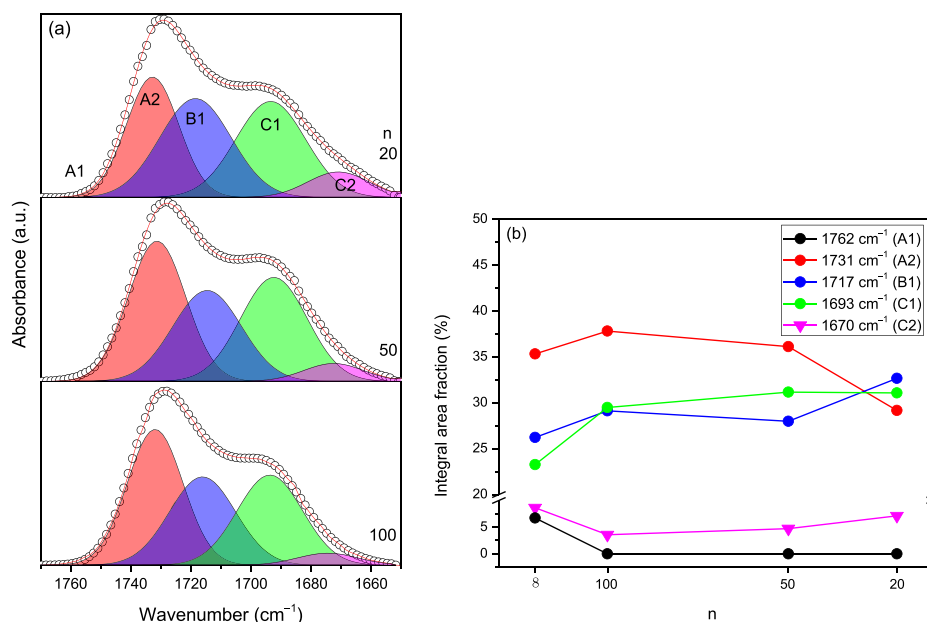


Fig. 8. (a) Results of the curve-fitting performed in the “amide I” region and (b) salt concentration dependence of the integral fraction of the resolved “amide I” bands (data for $n = \infty$ have been reproduced from [8]) of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids.

Fig. 8a shows the FT-IR spectra of d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids in the “amide I” region. Although no significant differences are seen in the global spectral profile for $n = 100$, 50, or 20, the inclusion of Mn(ClO₄)₂ into d-PCL(530)/siloxane led to changes in the environment of the C=O groups which are revealed in the “amide I” region in terms of band reorganization. The incorporation of increasing quantities of the guest salt ($n = 100$, 50 and 20) into the d-PCL(530)/siloxane host resulted in the complete saturation of the “free” C=O groups from the urethane cross-links (A1) and in a considerable reduction of the amount of “free” ester groups of the amorphous PCL(530) chains (A2) (Fig. 8b). In parallel the fraction of oxyethylene/urethane and urethane/urethane hydrogen-bonded aggregates (B1 and C1, respectively) increased significantly. The concentration of ester/urethane aggregates (C2) did not suffer, however, major changes over the whole salt concentration range studied.

The inspection of the spectral signature of the ClO₄[−] ion in the FT-IR spectra of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids allowed us gaining further insight into the local environment of the Mn²⁺ ions. This was made possible because the ClO₄[−] ion is one of the most extensively employed ions probes in spectroscopic analyses for the elucidation of ionic association [64]. As this ion has vibration modes that suffer characteristic changes (e.g., frequency shifts, splitting and/or intensity variations) upon coordination, it allows distinguishing the three main types of ionic species usually present in salt/polymer electrolytes: (a) high mobility “free” or weakly bonded ions; (b) low-mobility cations bonded strongly to the host polymer; (c) low-moderate mobility ionic aggregates (contact ion pairs and ionic multiplets).

The “free” ClO₄[−] ion (tetrahedral symmetry (T_d)) has nine vibrational degrees of freedom distributed between four normal Raman active modes: ν_1 (A1) (infrared inactive), ν_2 (E2) (infrared inactive), ν_3 (T2), and ν_4 (T2). These modes are expected at 931, 458, 1100 and 624 cm^{−1}, respectively [65,66]. Cation coordination lowers the ClO₄[−] ion local symmetry leading to band splitting of degenerate vibrations and to activation of infrared-forbidden modes. The strength of ion association is manifested in the magnitude of band separation and of the frequency shift. Mono- or tridentate coordination of the oxygen atoms of ClO₄[−] to a cation lowers the T_d symmetry to C_{3v} . As a consequence, the 3-fold

degenerate ν_3 and ν_4 vibrations split into two components (A1 and E), both in the infrared and Raman spectra. Bidentate coordination of the oxygen atoms of ClO₄[−] to a cation lowers the T_d symmetry to C_{2v} . The splitting of the 2-fold degenerate ν_2 vibration into two bands (A1 and A2) in the Raman spectrum and the splitting of the 3-fold degenerate ν_3 and ν_4 vibrations into three components (A1, B1, and B2) in the infrared and Raman spectra result.

In the present work we examined the ν_4 ClO₄ region of the FT-IR spectra of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrid samples (Fig. 9(a)). The results of the curve-fitting performed (Fig. 9(b) and Table 2) reveal that in the three samples studied the ClO₄[−] ions were either “free” or bonded to the Mn²⁺ ions along a bidentate configuration. The marked growth of the integral area fraction of the 632 cm^{−1} component (Fig. 9(c)) resulting from the incorporation of increasing amounts of Mn(ClO₄)₂ to the host hybrid matrix indicates that the proportion of bidentate ClO₄[−] ions increased. A major reduction in the fraction of “free” ions occurred concomitantly, as demonstrated by the dramatic decrease of the integral area fraction of the 625 cm^{−1} component.

3.5. Electron Paramagnetic Resonance (EPR)

Fig. 10 shows the X-band CW-EPR spectra measured at 50 K of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids with increasing salt concentration. In all the EPR spectra the signal consisted of a sextet with effective g -value $g \approx 2.0$ (centered at around 3300 G). The Mn²⁺ ion has a 3d⁵ electronic configuration, a spin $S = 5/2$, and ground state $^6S_{5/2}$. The lowest orbital level of the free ion is a singlet, which is six-fold degenerate in spin. An axial or tetragonal distortion of the octahedral crystal field splits this singlet into three Kramer's doublets: $\pm 5/2$, $\pm 3/2$, and $\pm 1/2$ [32,33]. The application of a magnetic field lifts the spin degeneracy of the Kramer's doublets, and as a consequence the resonances observed in the EPR spectra are due to transitions within the Kramer's doublets. The resonance at $g \approx 2.0$ is associated with Mn²⁺ ions in an environment close to octahedral symmetry and is believed to arise from transition within the $\pm 1/2$ Kramer doublet [67–70].

Mn has a stable isotope with non-zero nuclear spin (⁵⁵Mn) with $I = 5/2$ (100% natural abundance). The EPR spectra of the Mn²⁺ ions

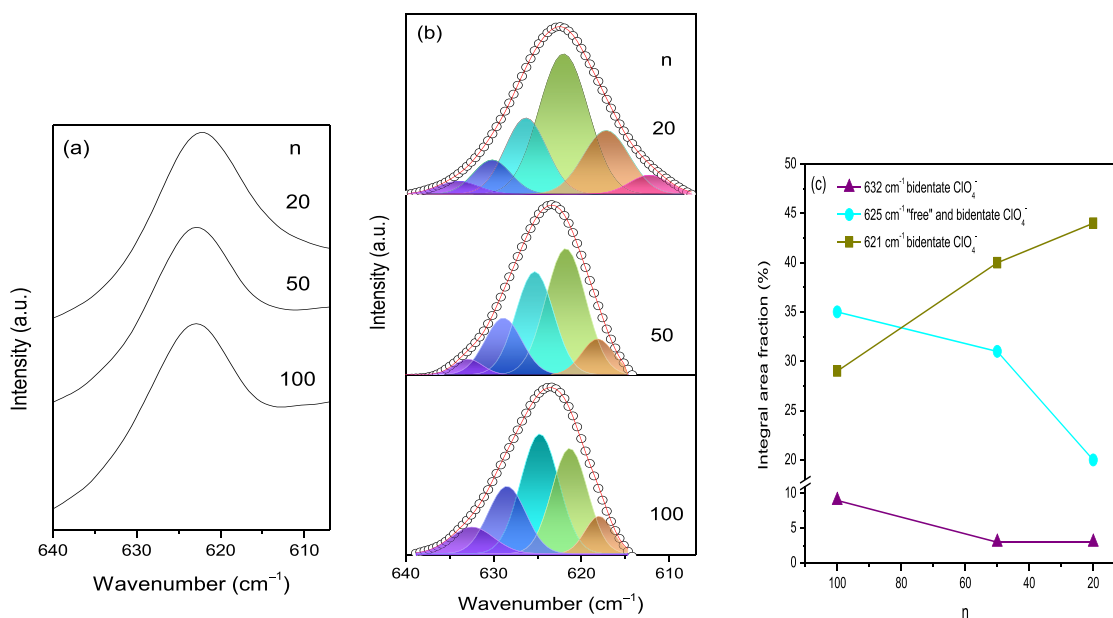


Fig. 9. (a) FT-IR spectra of the d-PLC(530)/siloxane_nMn(ClO₄)₂ biohybrids in the FT-IR $\nu_4\text{ClO}_4$ region; (b) Results of the curve-fitting; (c) Salt concentration dependence of the integral area fraction of selected $\nu_4\text{ClO}_4$ components (the lines drawn are just guides for the eyes).

at low Mn^{2+} concentration is further split into six lines by the hyperfine structure resulting from the dipole-dipole interaction between the magnetic moment of the ^{55}Mn nuclei and the electronic moment of the paramagnetic Mn^{2+} ion. The resonance at $g \approx 2.0$ is due to allowed $M_S = 1/2 \leftrightarrow -1/2$ magnetic dipolar transitions (selection rules $\Delta M_S = \pm 1$ and $\Delta m_I = 0$, where M_S and m_I are the electronic and nuclear spin state, respectively) from the $^6S_{5/2}$ ground state of Mn^{2+} .

The spectra of Fig. 10 are similar to those reported for disordered materials, such as glasses and polymers. The weak features between the spin-allowed hyperfine lines of the resonance signal were attributed to spin “forbidden” transitions ($\Delta M_S = \pm 1$, $\Delta m_I = \pm 1$) [71–73].

The EPR spectra of the Mn^{2+} ions in the d-PCL(530)/siloxane host can be qualitatively understood in terms of the spin-Hamiltonian for d^5 ions in axial symmetry [74]:

$$H = g\beta H \cdot S + D \left[S_z^2 - \frac{1}{3}S(S+1) \right] + AS \cdot I \quad (2)$$

where β is the Bohr magneton, H is the applied magnetic field, S is the spin component along the symmetry axis z , A is the hyperfine coupling constant, and the other symbols have their usual meaning. The first term in the Hamiltonian represents the interaction of the $S = 5/2$ electron spin with the external magnetic field H , i.e., the electron Zeeman interaction. For simplicity, the isotropic g -value was considered. The second term is the zero-field

splitting (ZFS) Hamiltonian and is characterized by the axial crystal field parameter D . The third term is the hyperfine interaction describing the interaction between the $S = 5/2$ electron spin with the $I = 5/2$ nuclear spin of the ^{55}Mn isotope.

The experimental Mn^{2+} EPR spectra were analyzed by numerical simulation of the spin Hamiltonian (Eq. (2)). Satisfactory fits to the experimental EPR spectra were obtained assuming two different Mn^{2+} species characterized by different coordination symmetries. The fit parameters for the species I included the g -value, A , and D . A strain parameter (specified by D -strain) was also introduced to account for the heterogeneity of the environments around the paramagnetic center, which results in broad distributions of the principal values of the D -tensor [43]. The Hamiltonian parameter $D = 612\text{--}661\text{ MHz}$ ($204\text{--}220 \times 10^{-4}\text{ cm}^{-1}$) deduced from the simulated spectra (Table 3) suggests that the Mn^{2+} ions of species I were complexed by the d-PCL(530)/siloxane matrix in an axially distorted coordination symmetry. The fit parameters for the species II included only g and A (i.e., $D = 0\text{ MHz}$). A strain parameter (noted as A strain) was used in samples with lower Mn^{2+} concentration ($n = 50$ and 100) to account for the distribution of A values. For simplicity, $S = 1/2$ for the simulations of species II was assumed. The Hamiltonian parameters obtained for species II suggests that these Mn^{2+} ions were not coordinated to the matrix. The simulated spectra, shown in Fig. 10, were obtained by adding the contribution from species I and II with the Hamiltonian parameters given in Table 3. The agreement between the observed and the calculated spectra is satisfactory, since the simulated spectra closely reproduce the position and the intensities of the most prominent features.

The value of the hyperfine constant has been correlated with the nature of the bonding character between the Mn^{2+} ions and its ligands in the hybrid electrolytes. The correlation, which is mainly determined by the electronegativity of the Mn^{2+} neighbors, was ascertained by Van Wieringen [75,76]. In covalent semiconductors like Mn-Te , A values are as low as $59 \times 10^{-4}\text{ cm}^{-1}$, while in fluorite crystals, where the bonding is ionic, $A \approx 97 \times 10^{-4}\text{ cm}^{-1}$ [35,77]. The magnitude of the hyperfine constant derived for the samples in the present work ($A \approx 90 \times 10^{-4}\text{ cm}^{-1}$, Table 2), suggests that the bonding between Mn^{2+} ions and the surrounding ligands is moderately ionic. This result is consistent with our previously

Table 2
Composition dependence of the integral area fraction (%) of the resolved components (cm^{-1}) of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids in the FT-IR $\nu_4\text{ClO}_4$ region.

n		50		20		Attribution [64,65]
ν	Area	ν	Area	ν	Area	
632	8.8	633	3.5	634	3.4	Bidentate ClO_4^-
628	19.4	629	16.5	630	8.3	Isotopic $^{37}\text{ClO}_4^-$
625	35.1	625	30.9	626	20.4	“Free” and bidentate ClO_4^-
621	28.8	622	40.2	622	44.2	Bidentate ClO_4^-
618	7.9	618	8.9	617	18.9	Isotopic $^{37}\text{ClO}_4^-$
–	–	–	–	612	4.7	non-assigned

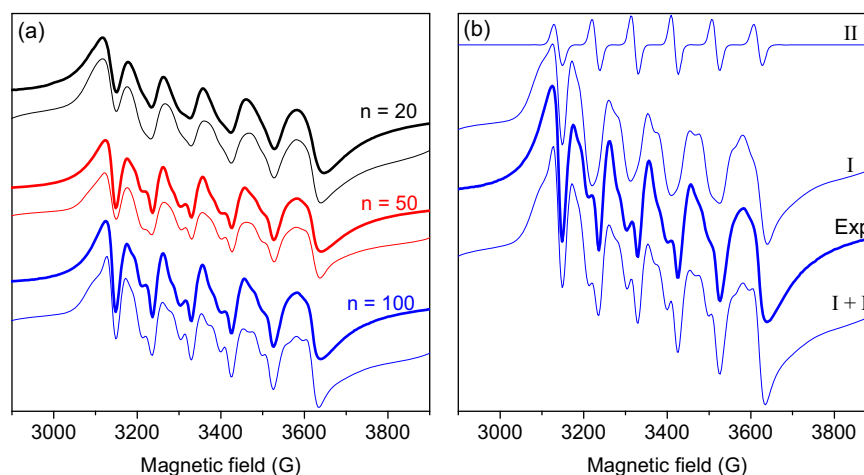


Fig. 10. (a) Experimental (bold lines) and simulated (normal lines) EPR spectra of d-PLC(530)/siloxane_nMn(ClO₄)₂ biohybrids (*n* = 20, 50, and 100), recorded at 50 K. (b) Experimental (thick line) and numerical simulation (thin lines) of the Mn²⁺ EPR signal for *n* = 100 considering species II, species I and full simulated spectrum (I + II).

Table 3

Summary of the spin Hamiltonian parameters of d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids obtained from the simulation of the experimental EPR spectra measured at 50 K. *Lwpp* refers to the peak-to-peak line width for isotropic broadening used for convolution of the CW-EPR spectrum. The first and second elements are the Gaussian and Lorentzian contributions, respectively. It should be noted that the *A* and *D* values are given in MHz units usually used in EPR simulation packages (conversion factor is 1 [cm⁻¹] = 0.33356 × 10⁻⁴ [MHz]).

Species		<i>n</i> = 100	<i>n</i> = 50	<i>n</i> = 20
I	Spin	5/2	5/2	5/2
	<i>g</i>	1.999	2.000	2.000
	<i>Lwpp</i> (mT)	1.4 1.1	2.4 0.67	1.5 2.3
	<i>A</i> (MHz)	272	272	272
	<i>D</i> (MHz)	631	618	579
	<i>D</i> strain (MHz)	656	661	612
II	Spin	1/2	1/2	1/2
	<i>g</i>	2.002	2.001	2.001
	<i>Lwpp</i> (mT)	1.7 0.0	1.8 0.0	2.0 0.37
	<i>A</i> (MHz)	268	269	269
	<i>A</i> strain (MHz)	15	20	–
	Absorption integral	253:1	261:1	447:1
I: II		9.475411	9.47674	9.474488

reported study of Cu²⁺-doped d-PCL(530)/siloxane-based electrolytes, where the molecular bonding coefficients α^2 and β^2 obtained by correlating the Cu²⁺ EPR spin Hamiltonian parameters and the optical absorption data suggested that bonding between the Cu²⁺ and its ligands was moderately ionic [59]. These conclusions are in perfect agreement with the FT-IR data reported in the previous section in which solid spectral evidences were found pointing out strong interaction between the Mn²⁺ ions and the C=O groups of the urethane cross-links and of the ester groups of the PCL(530) chains and also between the Mn²⁺ ions and the ClO₄⁻ ions. These two different cation environments might correspond to species I and II identified by EPR, respectively.

4. Conclusions

Paramagnetic amorphous d-PCL(530)/siloxane-based biohybrids doped with Mn(ClO₄)₂ were synthesized by sol-gel method. The incorporation of Mn²⁺ ions had a two-fold interest, endowing the resulting hybrids with ionic conductivity and paramagnetic properties. The ionic conductivity increased with salt concentration. The highest values were obtained for *n* = 20 (4.8×10^{-8} and 2.0×10^{-6} S cm⁻¹ at about 25 and 100 °C, respectively).

The hydrogen bonding interactions present in the d-PCL(530)/siloxane matrix were influenced by the inclusion of Mn(ClO₄)₂,

which promoted the formation of more oxyethylene/urethane and urethane/urethane aggregates. In the samples the Mn²⁺ ions interact with the “free” urethane and ester C=O groups of the host hybrid matrix host and also with the ClO₄⁻ ions along a bidentate configuration. “Free” ClO₄⁻ ions were also detected, although their concentration decreased, as expected, with salt content.

The magnitude of the EPR hyperfine constant of the analyzed samples ($A \approx 90 \times 10^{-4}$ cm⁻¹) is in agreement with the FT-IR data suggesting that the bonding between Mn²⁺ ions and the surrounding ligands is moderately ionic. The Mn²⁺ ions identified as species I are coordinated to the d-PCL(530)/siloxane matrix along an axially distorted coordination symmetry, whereas the Mn²⁺ bounded to ClO₄⁻ ions are classed as species II.

The ionic conducting, combined with the thermal stability up to at least 200 °C and the paramagnetic properties, open interesting prospects for the potential application of the d-PCL(530)/siloxane_nMn(ClO₄)₂ biohybrids in paramagnetic, photoelectrochemical and electrochromic devices.

Acknowledgements

This work was supported by Fundação para a Ciência e a Tecnologia (FCT) and Feder (contracts PTDC/CTM-BPC/112774/2009, PEst-OE/QUI/UI0616/2014 and PEst-C/QUI/UI0686/2013) and COST Action MP1202 “Rational design of hybrid organic-inorganic interfaces”. R.F.P.P. acknowledges FCT for a grant (SFRH/BPD/87759/2012). M.M.S. acknowledges CNPq (PVE grant 406617/2013-9), for a mobility grant. The financial support of the Brazilian agencies Capes and CNPq are gratefully acknowledged. Research was partially financed by the CeRTEV, Center for Research, Technology and Education in Vitreous Materials, FAPESP 2013/07793-6.

Appendix A. Supplementary data

Supplementary data associated with this article can be found, in the online version, at <http://dx.doi.org/10.1016/j.electacta.2016.06.088>.

References

- [1] F.M. Gray, *Polymer electrolytes*, Royal Society of Chemistry Cambridge (1997).
- [2] B.-Y. Chang, S.-M. Park, *Electrochemical Impedance Spectroscopy*, *Annu. Rev. Anal. Chem.* 3 (2010) 207–229.
- [3] M. Park, X. Zhang, M. Chung, G.B. Less, A.M. Sastry, A review of conduction phenomena in Li-ion batteries, *J. Power Sources* 195 (2010) 7904–7929.

- [4] C.J. Brinker, G.W. Scherer, The physics and chemistry of sol-gel processing, Academic Press, San Diego, 1990.
- [5] M. Fernandes, R. Leones, A.M.S. Costa, M.M. Silva, S. Pereira, J.F. Mano, E. Fortunato, R. Rego, V. de Zea Bermudez, Electrochromic devices incorporating biohybrid electrolytes doped with a lithium salt, an ionic liquid or a mixture of both, *Electrochim. Acta* 161 (2015) 226–235.
- [6] M. Fernandes, V.T. Freitas, S. Pereira, E. Fortunato, R.A.S. Ferreira, L.D. Carlos, R. Rego, V.D. Bermudez, Green Li⁺- and Er³⁺-doped poly(ε-caprolactone)/siloxane biohybrid electrolytes for smart electrochromic windows, *Sol. Energ. Mat. Sol. Cells* 123 (2014) 203–210.
- [7] S.C. Nunes, V. de Zea Bermudez, M.M. Silva, M.J. Smith, E. Morales, L.D. Carlos, R.A. Sá Ferreira, J. Rocha, Sol-gel derived Li⁺-doped poly(ε-caprolactone)/siloxane biohybrid electrolytes, *J. Solid State Electrochem.* 10 (2006) 203–210.
- [8] M. Fernandes, S.S. Nobre, L.C. Rodrigues, A. Gonçalves, R. Rego, M.C. Oliveira, R.A.S. Ferreira, E. Fortunato, M.M. Silva, L.D. Carlos, V.Z. d. Bermudez, Li⁺- and Eu³⁺-doped poly(ε-caprolactone)/siloxane biohybrid electrolytes for electrochromic devices, *ACS Appl. Mater. Interfaces* 3 (2011) 2953–2965.
- [9] M. Fernandes, L.C. Rodrigues, R.A.S. Ferreira, A. Gonçalves, E. Fortunato, M.M. Silva, M.J. Smith, L.D. Carlos, V. de Zea Bermudez, K⁺-doped poly(ε-caprolactone)/siloxane biohybrid electrolytes for electrochromic devices, *Solid State Ion.* 204–205 (2011) 129–139.
- [10] J.C.S. Teixeira, M. Fernandes, V. de Zea Bermudez, P.C. Barbosa, L.C. Rodrigues, M.M. Silva, M.J. Smith, Mg²⁺-doped poly(ε-caprolactone)/siloxane biohybrids, *Electrochim. Acta* 55 (2010) 1328–1332.
- [11] M. Fernandes, V. de Zea Bermudez, R.A. Sá Ferreira, L.D. Carlos, A. Charas, J. Morgado, M.M. Silva, M.J. Smith, Highly photostable luminescent poly(ε-caprolactone)/siloxane biohybrids doped with europium complexes, *Chem. Mat.* 19 (2007) 3892–3901.
- [12] M. Prabakaran, M.A. Rodriguez-Perez, J.A. de Saja, J.F. Mano, Preparation and characterization of poly(L-lactic acid)-chitosan hybrid scaffolds with drug release capability, *J. Biomed. Mater. Res. Part B Appl. Biomater.* 81B (2007) 427–434.
- [13] A. Kopytynska-Kasperczyk, P. Dobrzynski, M. Pastusiak, B. Jarzabek, W. Prochwicz, Local delivery system of doxycycline hyclate based on ε-caprolactone copolymers for periodontitis treatment, *Int. J. Pharm.* 491 (2015) 335–344.
- [14] A.G.A. Coombes, S.C. Rizzi, M. Williamson, J.E. Barralet, S. Downes, W.A. Wallace, Precipitation casting of polycaprolactone for applications in tissue engineering and drug delivery, *Biomaterials* 25 (2004) 315–325.
- [15] H.A. Declercq, T. Desmet, E.E.M. Berneel, P. Dubrue, M.J. Cornelissen, Synergistic effect of surface modification and scaffold design of bioplotting 3-D poly-ε-caprolactone scaffolds in osteogenic tissue engineering, *Acta Biomater.* 9 (2013) 7699–7708.
- [16] L. Elomaa, S. Teixeira, R. Hakala, H. Korhonen, D.W. Grijpma, J.V. Seppälä, Preparation of poly(ε-caprolactone)-based tissue engineering scaffolds by stereolithography, *Acta Biomater.* 7 (2011) 3850–3856.
- [17] T.R. Olsen, L.L. Davis, S.E. Nicolau, C.C. Duncan, D.C. Whitehead, B.A. Van Horn, F. Alexis, Non-invasive deep tissue imaging of iodine modified poly(caprolactone-co-1,4-oxepan-1,5-dione) using X-ray, *Acta Biomater.* 20 (2015) 94–103.
- [18] S.-H. Teng, P. Wang, J.-Q. Dong, Bioactive hybrid coatings of poly(ε-caprolactone)-silica xerogel on titanium for biomedical applications, *Mater. Lett.* 129 (2014) 209–212.
- [19] Y. Niu, K.C. Chen, T. He, W. Yu, S. Huang, K. Xu, Scaffolds from block polyurethanes based on poly(ε-caprolactone) (PCL) and poly(ethylene glycol) (PEG) for peripheral nerve regeneration, *Biomaterials* 35 (2014) 4266–4277.
- [20] V. Mkhabela, S.S. Ray, Biodegradation and bioresorption of poly(ε-caprolactone) nanocomposite scaffolds, *Int. J. Biol. Macromol.* 79 (2015) 186–192.
- [21] T. Takeda, R.-J. Xie, N. Hirotsaki, Y. Matsushita, T. Honma, Manganese valence and coordination structure in Mn,Mg-codoped γ-AlON green phosphor, *J. Solid State Chem.* 194 (2012) 71–75.
- [22] S.G. Kim, S.H. Lee, N.H. Park, H.L. Park, K.W. Min, S.I. Mho, T.W. Kim, Y.H. Hwang, Mn²⁺ site behaviors in Cd₂Zn_{1-x}Ga₂O₄ and Sr_xBa_{1-x}Al₁₂O₁₉ green phosphors, *Solid State Commun.* 110 (1999) 515–518.
- [23] V. Singh, R.P.S. Chakradhar, J.L. Rao, H.-Y. Kwak, Investigations on green-emitting, Mn²⁺: BaAl₁₂O₁₉ phosphors obtained by solution combustion process, *J. Mater. Sci.* 46 (2011) 3928–3934.
- [24] G.V.M. Williams, S. Schweizer, B. Henke, C. Dunford, A. Edgar, X-ray and UV induced photo-luminescence from RbCdF₃:Mn²⁺, *Curr. Appl. Phys.* 6 (2006) 351–354.
- [25] X. Zhang, H. Zeng, Q. Su, Mn²⁺-doped Ba₂ZnS₃ phosphor as a potential luminescent material for white LEDs, *J. Alloys Compd.* 441 (2007) 259–262.
- [26] Y. Hao, Y. Wang, Luminescent properties of Zn₂SiO₄:Mn²⁺ phosphor under UV, VUV and CR excitation, *J. Lumines.* 122–123 (2007) 1006–1008.
- [27] X.-J. Wang, D. Jia, W.M. Yen, Mn²⁺ activated green, yellow, and red long persistent phosphors, *J. Lumines.* 102–103 (2003) 34–37.
- [28] J.A. Hernández, E.G. Camarillo, G. Muñoz, C.J. Flores, E.B. Cabrera, F. Jaque, J.J. Romero, J. García Solé, H.S. Murrieta, Red and green fluorescence of Mn²⁺ in NaCl, *Opt. Mater.* 17 (2001) 491–495.
- [29] G. Härkönen, M. Leppänen, E. Soininen, R. Törnqvist, J. Viljanen, Multicolour thin film electroluminescent displays: a new application of rare earth metals, *J. Alloys Compd.* 225 (1995) 552–554.
- [30] K. Kang, S.H. Huang, X.W. Huang, W.D. Zhuang, F.T. You, S.S. Zhang, H.Q. He, Preparation for a new green-emitting phosphor for cold cathode fluorescent lamp, *J. Lumines.* 122–123 (2007) 804–807.
- [31] Y.-Y. Wang, T. Li, Y.-X. Qi, R.-L. Bai, L.-W. Yin, H. Li, N. Lun, Y.-J. Bai, Carbon-coated manganese silicate exhibiting excellent rate performance and high-rate cycling stability for lithium-ion storage, *Electrochim. Acta* 186 (2015) 572–578.
- [32] A. Abragam, B. Bleaney, Electron paramagnetic resonance of transition ions, Oxford University Press, Oxford, 1970.
- [33] J.W. Orton, Electron paramagnetic resonance, Gordon & Breach Sc. Publ. Inc., New York, 1969.
- [34] J.R. Pilbrow, Transition ion electron paramagnetic resonance, Clarendon Press, Oxford, 1990.
- [35] D. Möncke, E.I. Kamitsos, A. Herrmann, D. Ehrt, M. Friedrich, Bonding and ion-ion interactions of Mn²⁺ ions in fluoride-phosphate and boro-silicate glasses probed by EPR and fluorescence spectroscopy, *J. Non-cryst. Solids* 357 (2011) 2542–2551.
- [36] A.V.R. Kumar, C.S. Rao, N.N. Rao, V.R. Kumar, I.V. Kityk, N. Veeraiah, Influence of valence and coordination of manganese ions on spectral and dielectric features of Na₂SO₄-B₂O₃-P₂O₅ glasses, *J. Non-Cryst. Solids* 358 (2012) 1278–1286.
- [37] A. Moguš-Milanković, L. Pavić, K. Srilatha, C. Srinivasa Rao, T. Srikumar, Y. Gandhi, N. Veeraiah, Electrical, dielectric and spectroscopic studies on MnO doped LiI-AgI-B₂O₃ glasses, *J. Appl. Phys.* 111 (2012) 013714.
- [38] R. Ganesan, B. Viswanathan, Redox properties of bis(8-hydroxyquinoline) manganese(II) encapsulated in various zeolites, *J. Mol. Catal. A-Chem.* 223 (2004) 21–29.
- [39] D.E. De Vos, B.M. Weckhuysen, T. Bein, ESR fine structure of manganese ions in zeolite A detects strong variations of the coordination environment, *J. Am. Chem. Soc.* 118 (1996) 9615–9622.
- [40] T.H. Bennur, D. Srinivas, P. Ratnasamy, EPR spectroscopy of copper and manganese complexes encapsulated in zeolites, *Microporous Mesoporous Mat.* 48 (2001) 111–118.
- [41] V.G. Makhankova, A.O. Beznischenko, V.N. Kokozay, R.I. Zubatyuk, O.V. Shishkin, J. Jezierska, A. Ozarowski, Direct synthesis, crystal structures, high-field EPR, and magnetic studies of heterometallic polymers containing manganese(II) carboxylates interconnected by [Cu(en)₂]²⁺, *Inorg. Chem.* 47 (2008) 4554–4563.
- [42] PeakFit, Systat Software, Inc., www.systat.com/products/PeakFit/.
- [43] S. Stoll, A. Schweiger, EasySpin, a comprehensive software package for spectral simulation and analysis in EPR, *J. Magn. Reson.* 178 (2006) 42–55.
- [44] K.H. Stern, High temperature properties and thermal decomposition of inorganic salts with oxyanions, CRC Press, London, 2000.
- [45] J. Hetmańczyk, Ł. Hetmańczyk, A. Migdał-Mikuli, E. Mikuli, Thermal properties of polycrystalline [Mn(NH₃)₆](ClO₄)₂, *J. Therm. Anal. Calorim.* 118 (2014) 1049–1056.
- [46] T.F. Scientific, Manganese(II) perchlorate hexahydrate, Cat No. AC316510000 [Online], Fair Lawn, New Jersey, USA, 2015.
- [47] L.D. Carlos, V. de Zea Bermudez, R.A. Sá Ferreira, L. Marques, M. Assunção, Sol-gel derived urea cross-linked organically modified silicates. 2. Blue-light emission, *Chem. Mat.* 11 (1999) 581–588.
- [48] C. Fernández-Sánchez, C.J. McNeil, K. Rawson, Electrochemical impedance spectroscopy studies of polymer degradation: application to biosensor development, *Trac-Trends Anal. Chem.* 24 (2005) 37–48.
- [49] D.G. Han, G.M. Choi, Simulation of impedance for 2-D composite, *Electrochim. Acta* 44 (1999) 4155–4161.
- [50] M. Watanabe, M. Togo, K. Sanui, N. Ogata, T. Kobayashi, Z. Ohtaki, Ionic conductivity of polymer complexes formed by poly(β-propiolactone) and lithium perchlorate, *Macromolecules* 17 (1984) 2908–2912.
- [51] E. Barsoukov, J.R. Macdonald, Impedance Spectroscopy: Theory, Experiment, and Applications, 2nd ed., Wiley, New York, 2005.
- [52] B.A. Boukamp, A package for impedance/admittance data analysis, *Solid State Ion.* 18 (1986) 136–140.
- [53] B.A. Boukamp, A Nonlinear Least Squares Fit procedure for analysis of impedance data of electrochemical systems, *Solid State Ion.* 20 (1986) 31–44.
- [54] F.M. Gray, Transport Properties: Effects of Dynamic Disorder, Solid Polymer Electrolytes: Fundamentals and Technological Applications, VCH Publishers Inc., New York, USA, 1991.
- [55] M.A. Ratner, D.F. Shriver, Ion transport in solvent-free polymers, *Chem. Rev.* 88 (1988) 109–124.
- [56] S.C. Nunes, V.D. Bermudez, M.M. Silva, M.J. Smith, D. Ostrovskii, R.A.S. Ferreira, L.D. Carlos, J. Rocha, A. Gonçalves, E. Fortunato, Sol-gel-derived potassium-based di-ureasils for smart windows, *J. Mater. Chem.* 17 (2007) 4239–4248.
- [57] R.D. Alves, L.C. Rodrigues, J.R. Andrade, M. Fernandes, J.V. Pinto, L. Pereira, A. Pawlicka, R. Martins, E. Fortunato, V. de Zea Bermudez, M.M. Silva, Gelatin/Zn(CF₃SO₃)₂ polymer electrolytes for electrochromic devices, *Electroanalysis* 25 (2013) 1483–1490.
- [58] L.C. Rodrigues, M.M. Silva, M.J. Smith, A. Gonçalves, E. Fortunato, Poly(ε-caprolactone)/siloxane biohybrids with application in “smart windows”, *Synth Met.* 161 (2012) 2682–2687.
- [59] R. Leones, J.P. Donoso, C.J. Magon, I.D.A. Silva, A.S.S. de Camargo, A. Pawlicka, M. Silva, Ionic, paramagnetic and photophysical properties of a new biohybrid material incorporating copper perchlorate, *Electrochim. Acta* 173 (2015) 76–81.
- [60] C.B. Ferreira, M. Fernandes, L.C. Rodrigues, M.M. Silva, M.J. Smith, V. de Zea Bermudez, Vibrational analysis of d-PCL(530)/siloxane-based hybrid electrolytes doped with two lithium salts, *Ionics* 19 (2013) 1803–1809.
- [61] Y. He, Y. Inoue, Novel FTIR method for determining the crystallinity of poly(ε-caprolactone), *Polym. Int.* 49 (2000) 623–626.

- [62] A. Sanchis, M.G. Prolongo, C. Salom, R.M. Masegosa, Melting behavior, miscibility, and hydrogen-bonded interactions of poly(ϵ -caprolactone)/poly(4-hydroxystyrene-co-methoxystyrene) blends, *J. Polym. Sci. Pt. B-Polym. Phys.* 36 (1998) 95–104.
- [63] V. de Zea Bermudez, D. Ostrovskii, M.C. Goncalves, L.D. Carlos, R.A. Sa Ferreira, L. Reis, P. Jacobsson, Urethane cross-linked poly(oxyethylene)/siliceous nanohybrids doped with Eu^{3+} ions Part 1. Coordinating ability of the host matrix, *Phys. Chem. Chem. Phys.* 6 (2004) 638–648.
- [64] S.C. Nunes, V. de Zea Bermudez, D. Ostrovskii, P.B. Tavares, P.C. Barbosa, M.M. Silva, M.J. Smith, Spectroscopic and structural studies of di-ureasils doped with lithium perchlorate, *Electrochim. Acta* 53 (2007) 1466–1475.
- [65] M. Chabanel, D. Legoff, K. Touaj, Aggregation of perchlorates in aprotic donor solvents. Part 1.–Lithium and sodium perchlorates, *J. Chem. Soc. –Faraday Trans.* 92 (1996) 4199–4205.
- [66] S.D. Ross, Forbidden transitions in the infra-red spectra of some tetrahedral anions – I. perchlorates, *Spectrosc. Acta* 18 (1962) 225–228.
- [67] M.S. Reddy, G. Murali Krishna, N. Veeraiah, Spectroscopic and magnetic studies of manganese ions in $\text{ZnO-Sb}_2\text{O}_3\text{-B}_2\text{O}_3$ glass system, *J. Phys. Chem. Solids* 67 (2006) 789–795.
- [68] P. Pascuta, M. Bosca, G. Borodi, E. Culea, Thermal, structural and magnetic properties of some zinc phosphate glasses doped with manganese ions, *J. Alloys Compd.* 509 (2011) 4314–4319.
- [69] V. Vamsi Priya, G. Upender, M. Prasad, FTIR and ESR studies of VO^{2+} and Mn^{2+} doped glasses of system $59\text{B}_2\text{O}_3\text{-}10\text{As}_2\text{O}_3\text{-(}30-x\text{)PbO-xBaO}$, *Glass Phys. Chem.* 40 (2014) 144–150.
- [70] R. Kripal, M. Maurya, Characterization of Mn^{2+} doped tetramethylammoniumtetrachlorozincate single crystal using EPR and optical absorption, *Mater. Chem. Phys.* 108 (2008) 257–262.
- [71] H.W. de Wijn, R.F. van Balderen, Electron spin resonance of manganese in borate glasses, *J. Chem. Phys.* 46 (1967) 1381–1387.
- [72] V. Černý, B. Petrová, M. Frumar, EPR spectra of Mn^{2+} doped $\text{CdX}_2\text{-PbY}_2\text{-KI}$ (X, Y = Cl Br) glasses, *J. Non-Cryst. Solids* 125 (1990) 17–24.
- [73] A. Ciechanowska, J. Hanuza, E. Stanisławska, E. Kociolek-Balawejder, Synthesis of polymer-based hybrid materials via Mn(II) oxidation with N-bromosulphonamide polymer and their characterization, *J. Mater. Sci.* 50 (2015) 4300–4311.
- [74] P.A. Gonzalez Beermann, B.R. McGarvey, S. Muralidharan, R.C.W. Sung, EPR spectra of Mn^{2+} -doped ZnS quantum dots, *Chem. Mat.* 16 (2004) 915–918.
- [75] J.S. van Wieringen, Paramagnetic resonance of divalent manganese incorporated in various lattices, *Discuss. Faraday Soc.* 19 (1955) 118–126.
- [76] E. Šimánek, K.A. Müller, Covalency and hyperfine structure constant A of iron group impurities in crystals, *J. Phys. Chem. Solids* 31 (1970) 1027–1040.
- [77] R.W.A. Franco, J.F. Lima, C.J. Magon, J.P. Donoso, Y. Messaddeq, Magnetic resonance study of the crystallization behavior of InF_3 -based glasses doped with Cu^{2+} , Mn^{2+} and Gd^{3+} , *J. Non-Cryst. Solids* 352 (2006) 3414–3422.