



Synthetic polycrystals of CaSiO_3 un-doped and Cd, B, Dy, Eu-doped for gamma and neutron detection

Carlos D. Gonzales-Lorenzo^{a,*}, Shiguo Watanabe^{a,*}, Nilo F. Cano^{b,*}, Jorge S. Ayala-Arenas^{c,*}, Carmen C. Bueno^{d,*}

^a Instituto de Física, Universidade de São Paulo, Rua do Matão, Travessa R, 187, CEP 05508-090 São Paulo, SP, Brazil

^b Instituto do Mar, Universidade Federal de São Paulo, Rua Doutor Carvalho de Mendonça, 144, CEP 11070-100 Santos, SP, Brazil

^c Escuela Profesional de Física, Facultad de Ciencias Naturales y Formales, Universidad Nacional de San Agustín (UNSA), Av. Independencia S/N, Arequipa, Peru

^d Instituto de Pesquisas Energéticas e Nucleares, IPEN-CNEN/SP, Av. Prof. Lineu Prestes, 2242, Cidade Universitária, 05508-000 São Paulo, SP, Brazil

ARTICLE INFO

Keywords:

CaSiO_3

Gamma and neutron dosimetry

Thermoluminescence

ABSTRACT

The undoped and B, Cd, Dy, Eu doped synthetic CaSiO_3 polycrystals were produced in the laboratory. They are very sensitive γ -ray detectors with main prominent TL peak occurring at about 270 °C, this peak was obtained using 4 °C/s heating rate. The TL behavior changes very little by doping with B, Cd and Dy while Eu doping brings changes. These minerals can be used also for neutron dosimetry. Thermal neutrons react with Ca, Si and O through (n, γ) process and γ emitted in this reaction added to γ -rays of the reactor that produces thermal neutrons and are responsible for induction of thermoluminescence. The TL response of CaSiO_3 is linear for dose < 10 Gy and then has a supralinear behavior up to about 7 kGy and saturating beyond.

1. Introduction

The development and study of new radiation dosimeters have been published in the past [1–16]. In fact, a large number of materials have been investigated as to their sensitivity as thermoluminescent phosphors. Of course, other physical properties have also been investigated to be used for radiation dosimetry, such as electron spin resonance, optically stimulated luminescence, etc. [17–19]. Concerning TL dosimeter, it is desirable that it detects not only electromagnetic radiation, but also charged accelerated particles as well as neutrons. Neutrons are detected through nuclear reaction with atoms in the detector. While very low energy neutrons with energy smaller than few keV interact with any element through (n, γ) reaction [20], higher energy neutrons can have reactions involving protons or even larger particles. When the (n, γ) reaction takes place, the nucleus of the element absorbs a neutron and the isotope formed drops to the ground state by the gamma emission. The detector absorbs all or part of these emitted γ -rays which induces TL on the dosimeter.

In nature, a large amount of the so called silicate minerals are found. They are very sensitive concerning the thermoluminescence is considered. Hence they are good radiation dosimeters. Beryl, tourmaline, quartz, jadeite are good examples. Natural wollastonite is CaSiO_3 silicate mineral that has been investigated as a possible material for

radiation dosimetry [21,22].

This paper concerns synthetic CaSiO_3 for electromagnetic radiation and neutrons detection. There are, of course, natural wollastonites.

There are three structural modifications of wollastonite: (1) pseudowollastonite (β - CaSiO_3) the high temperature form, it is crystallized in triclinic symmetry; (2) wollastonite-2M and (3) wollastonite-Tc. These two last ones are referred to as low temperature form, also considered (α - CaSiO_3) [23]. While wollastonite-2M is monoclinic, wollastonite-Tc is triclinic. Fig. 1 show the structure of wollastonite-Tc projected in z-plane [24]. The chains of SiO_4 -tetrahedra and Ca atoms are shown.

Yamanaka and Mori [25] studied the structure of a pseudowollastonite crystal showing that it is characterized by four layers, one of which is composed of ternary rings of three tetrahedra of SiO_4 and a seemingly octahedral layer. Hesse [26] found that the structure of wollastonite-2M is monoclinic with space group $P2_1/a$, $a = 15.409$. Yang and Prewitt [27] using XRD have shown that pseudowollastonite is the high temperature form of CaSiO_3 , above 1125 °C and commonly occurs in slags, cement and ceramic materials. It has monoclinic $C2/c$ symmetry. Souza et al. [28,29] used pellets of mixed wollastonite and teflon and irradiated them with x-rays. The TL glow curve presented peaks at 85 °C and 200 °C, the second one being the prominent one. Kulkarni et al. [30] produced nanocrystalline β - CaSiO_3 by low

* Corresponding authors.

E-mail addresses: clorenzo@if.usp.br (C.D. Gonzales-Lorenzo), watanabe@if.usp.br (S. Watanabe), nilocano@if.usp.br, nilo.cano@unifesp.br (N.F. Cano), jayala@unsa.edu.pe (J.S. Ayala-Arenas), ccbueno@ipen.br (C.C. Bueno).

<https://doi.org/10.1016/j.jlumin.2018.04.037>

Received 7 January 2018; Received in revised form 29 March 2018; Accepted 16 April 2018

Available online 17 April 2018

0022-2313/ © 2018 Elsevier B.V. All rights reserved.

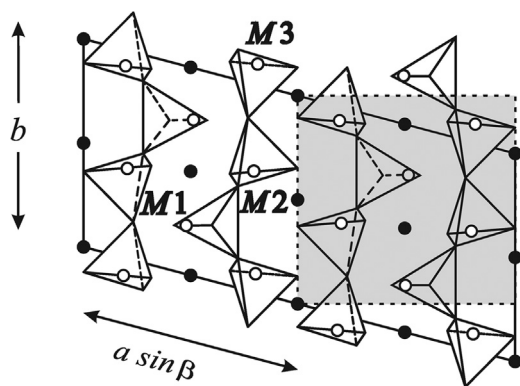


Fig. 1. Structure of wollastonite-Tc projected on (a, b) -plane showing SiO_4 -tetrahedra chains. White circles (o) are Ca-ions. The dashed area is that described as having pseudomonoclinic symmetry. (After [24]).

temperature combustion method. Its TL glow curve showed a shoulder peak at 175 °C and prominent peak at 230 °C. The deconvolution has shown that high temperature peak is a superposition of 208 and 242 °C peaks.

2. Materials and methods

The synthesis process to produce an artificial pure CaSiO_3 polycrystals starts with weighing stoichiometric quantities of reagent grade CaO and SiO_2 . In the present, we used 12.0 g (48.3 wt%) CaO and 12.8 g (51.7 wt%) of SiO_2 . It then placed in an oven heated to 1500 °C to melt the above mixture, for two hours. The melt is then cooled slowly using a temperature controller so that the room temperature is reached after about 24 h. This process produces a polycrystalline material. To produce doped CaSiO_3 , before melting 392 ppm Cd, 135 ppm B, 500 ppm Dy, and 1000 ppm Eu was added in each batch.

These polycrystalline samples of CaSiO_3 doped and undoped were crushed and sieved to retain grains 0.080–0.180 mm in size for TL measurements, while grains smaller than 0.080 mm in diameter were used in the X-rays diffraction analysis.

TL measurements were carried out using Harshaw TL reader model 4500 in a nitrogen atmosphere; the heating rate was kept at 4 °C/s. Each point in the glow curve is an average of five readings.

The irradiations for low dose of the order of mGy and high doses in the region of hundreds of Gy were done at the Radiations Technology Center (CTR) of the Institute for Energy and Nuclear Researches (IPEN) using a ^{60}Co source type gamma-cell with a dose rate of 0.739 kGy/h, and a panoramic type source with a dose rate of 9.10 Gy/h at 40 cm from the source. For very low dose irradiation (mGy), was used a ^{137}Cs source of 662 keV gamma rays and with a dose rate of 9.54 mGy/s at 30 cm from the source. The γ -irradiation was performed at room temperature and under conditions of electronic equilibrium.

The research reactor IEA-R1 belonging to the Institute for Energy and Nuclear Researches is a swimming pool type reactor operating at 5 MW power. Fig. 2 shows approximate Normalized differential Flux Density $\phi'(E)$ of neutrons in $\text{cm}^{-2}\text{s}^{-1}\text{eV}^{-1}$ of a research reactor, adapted from [31]. Thermal neutrons are considered those with energy < 0.5 eV.

Synthetic, pure, polycrystals of CaSiO_3 with grains size selected between 0.080 and 0.180 mm sizes were sealed in silica tubes each of about 4 mm diameter and 20 mm long. Each such tube has been placed inside a somewhat larger aluminum tube to be irradiated in a position called 13B inside IEA-R1. For technical reason the irradiation was carried out in two different periods: in the first the detectors were irradiated with (6.0, 15, 30, 60) $\times 10^{13}$ n/cm²; in the second with (2.1 and 30) $\times 10^5$ n/cm² fluences in two different positions.

The pure and doped polycrystals of CaSiO_3 were irradiated in

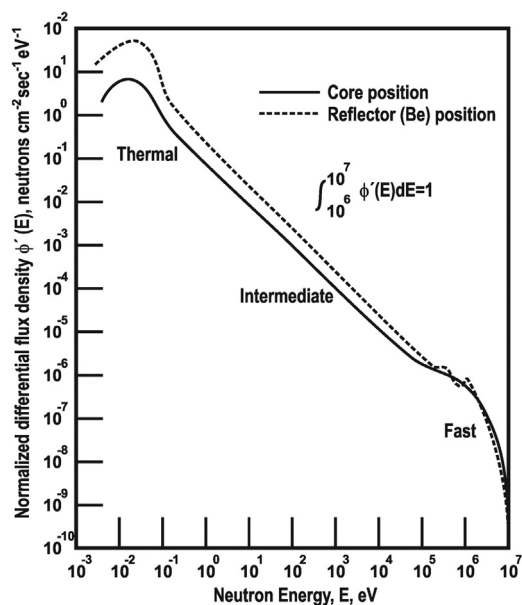


Fig. 2. Neutrons flux in a research reactor.

thermal (largest portion), epithermal (smaller portion) and fast neutrons (very small fraction). Since thermal and epithermal neutrons interact with Ca, Si and O through (n, γ) reaction and out coming γ that induces TL in the dosimeters what we are measuring is essentially thermal and epithermal effects

3. Results and discussion

The diffractograms of the undoped, and Cd, B and Dy doped polycrystals are shown in Fig. 3. Comparing the powder XRD pattern to the 96-901-1914 and 96-900-2180 files of the Match Program, all the peaks of the polycrystals were identified as belonging to wollastonite-2M (CaSiO_3 undoped) and pseudowollastonite (for Cd, B, Dy and Eu doped), respectively. This result shows that the polycrystals obtained by the devitrification method is adequate to obtain polycrystals with crystalline structure of the wollastonite.

The dose response of synthetic materials for dosimetry applications is a very important property. An ideal dosimeter should have linear behavior for all dose range. In order to determine the dose response of the un-doped, and Cd, B, Dy and Eu doped samples from low dose of the order of mGy up to high dose (kGy), the samples in powder form were irradiated with different gamma-doses.

Just for practical purpose let us assume in this paper that wollastonite refers to natural minerals and CaSiO_3 to synthetic polycrystals.

The undoped samples irradiated with doses higher than about 10 mGy presented TL peaks at 270 °C. TL glow curves of undoped CaSiO_3 samples irradiated with low dose between 10 mGy and 1 Gy are shown in Fig. 4(a). Fig. 4(b) shows the glow curves of CaSiO_3 undoped and irradiated with gamma rays with doses larger than 5 Gy up to 50 kGy. This results show that the synthetic pure CaSiO_3 is a very sensitive ionic crystal as far as its thermoluminescence is concerned and to wide range of gamma-rays dose, from mGy to 30–50 kGy.

Fig. 5 shows the TL response of the main TL peak for doses ranging from mGy to kGy range. Analyzing the dose response curves with log axes in the same scale, as shown in Fig. 5, it can be observed that the TL response of peak at 270 °C has a linear behavior as the curve slope equals to 45° in the dose range from few cGy up to about few Gy and after that TL response is supralinear up to about 7 kGy and then it saturates. This means that we have here a detector that responds from few cGy to 7 kGy.

As to the models that explain supralinearity there are, in fact, many.

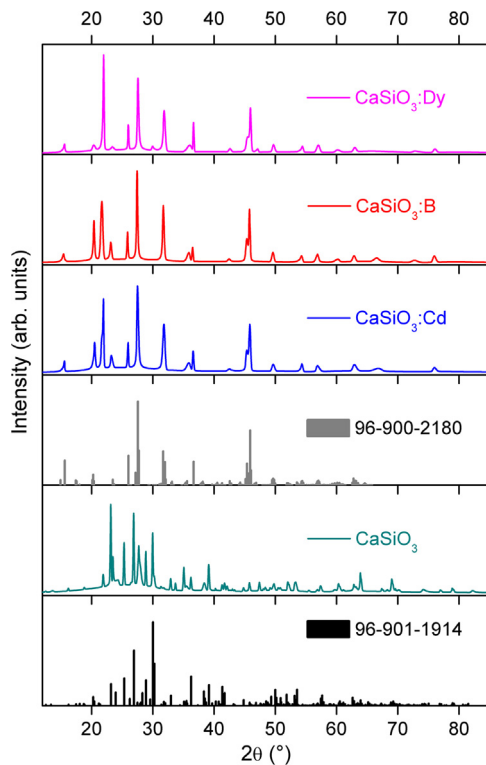


Fig. 3. XRD pattern of CaSiO_3 and CaSiO_3 doped with Ca, B and Dy produced in this work, to be compared with XRD patterns from Archive 96-901-1914 (wallastonite-2M) and 96-900-2180 (pseudowollastonite) - program Match!.

Broadly, they are divided into that is assumed to happen in the irradiation stage and the other during heating for reading TL.

One of the first models was introduced by Cameron and Zimmerman [32]; it assumes that besides existing TL traps the irradiation creates new traps that are responsible for supralinearity. Cameron and Zimmerman [33] proposed a model in which the radiation create new centers of recombination. Suntharalingam and Cameron [34] proposed competing trap model. The track interaction was introduced by Claffy et al. [35], but Mische and McKeever [36] introduced track interaction model different from that of Claffy et al. [35].

The reproducibility of the dosimeters can be affected after repeated usage [37]; therefore, this is one of the most important factors for dosimeter materials. For analysis the reproducibility of undoped synthetic CaSiO_3 polycrystals sample, 1.8 mg of sample in powder form was irradiated with 1.0 Gy of test dose, read and annealed, and irradiated again; this procedure was repeated four times to the same sample. The Fig. 6 shows the reproducibility and the sensitivity by intensity of peak at 270 °C, decreasing by 18% after of first sequence of radiation-reading-annealed during the procedure of TL readout.

Another important property of any TL material is the fading [38]. We irradiated CaSiO_3 with 1 Gy γ -rays and kept it in the dark. Its TL was read out after, one, two, etc. hours up to 32 days. The result is shown in Fig. 7. It shows that there is decay is about 20% in the first 2–3 h, but after that there is no decay. Therefore, we say CaSiO_3 has small fading.

To compare with the glow curves from undoped samples, in Fig. 8, the glow curves of doped synthetic samples with Cd, B and Dy and irradiated between 0.5 and 50 kGy are presented. The pure sample has shown peak around 270 °C. This result indicates that this TL peak in CaSiO_3 is due to intrinsic defects.

In a silicate crystal, it is known that oxygen vacancies are produced at room temperature [39,40]. Under irradiation, for example, with ^{60}Co γ -rays two facts occur. First, it creates a large number of electron-hole pairs and two electrons are captured by oxygen vacancy. Second, the radiation produces new oxygen vacancies that capture electrons. The

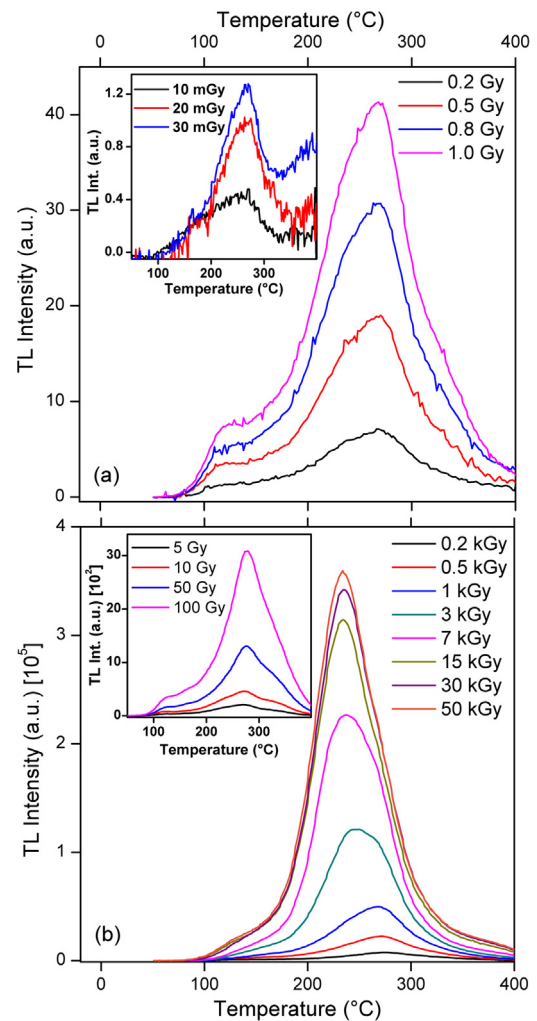


Fig. 4. (a) TL glow curves of CaSiO_3 irradiated with low γ -ray doses of 10 mGy up to 1.0 Gy using a mass about 5.6 mg. (b) TL glow curves of CaSiO_3 irradiated with γ -ray doses (^{60}Co source) of 5 Gy up to 50 kGy using a mass about 1.8 mg.

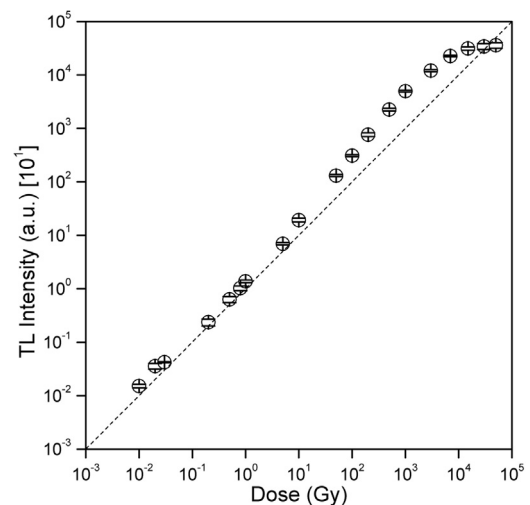


Fig. 5. TL intensity behavior of the 250–270 °C peak as a function of gamma radiation doses, the dashed line indicates linearity. In the inset of the figure, the TL intensity versus doses of the TL peaks at 270 °C for low dose irradiation is shown.

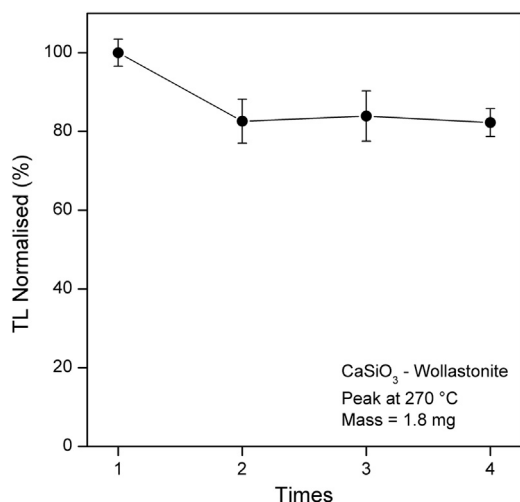


Fig. 6. Reproducibility of TL response of undoped CaSiO_3 synthetic irradiated with 1 Gy of ^{60}Co .

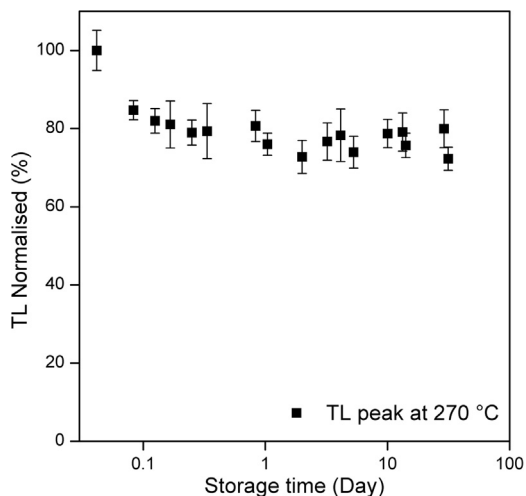


Fig. 7. TL intensity of the samples irradiated with 1 Gy against the storage time at room temperature for the undoped wollastonite.

radiation also creates aluminum centers, $[\text{AlO}_4/\text{h}]$ [18]. With heating crystal up to 300°C , one electron from oxygen vacancy with two electrons is liberated creating E'_1 -center which is one oxygen-vacancy with one electron. Above 300°C the remaining electron is liberated. These liberated electrons recombine with holes in the aluminum center and emit TL light (TL peaks) [41].

In Fig. 9 glow curves of $\text{CaSiO}_3:\text{Eu}$ are shown for radiation doses from 0.5 up to 1200 kGy. Although the glow curves shown in Fig. 9 exhibit three peaks as in B, Cd, Dy doped CaSiO_3 , Fig. 8. We note that there is the following difference, in Eu doped CaSiO_3 the peak 3 is prominent while in other cases the peak 2 is very intense compared to peak 3. Nothing was found in the literature about this effect of adding 1000 ppm Eu as impurity. This will be subject of future work.

Fig. 10(a) shows glow curves of undoped CaSiO_3 irradiated with thermal neutrons with fluence indicated in the figure. Fig. 10(b) shows glow curves of $\text{CaSiO}_3:\text{Dy}$ irradiated with neutrons with fluence as indicated in the figure. Similar glow curves are exhibited by CaSiO_3 doped with B and Cd. Compared to the glow curve of undoped CaSiO_3 , it is to be noted that the doping induces smaller peaks around $120\text{--}125^\circ\text{C}$ and other one around 375°C . Now Fig. 10(c) shows glow curves of $\text{CaSiO}_3:\text{Eu}$, which is essentially the same as that of Eu-doped CaSiO_3 irradiated with gamma-rays. Fig. 10(d) presents TL intensity as function of neutron fluence in linear-log scale.

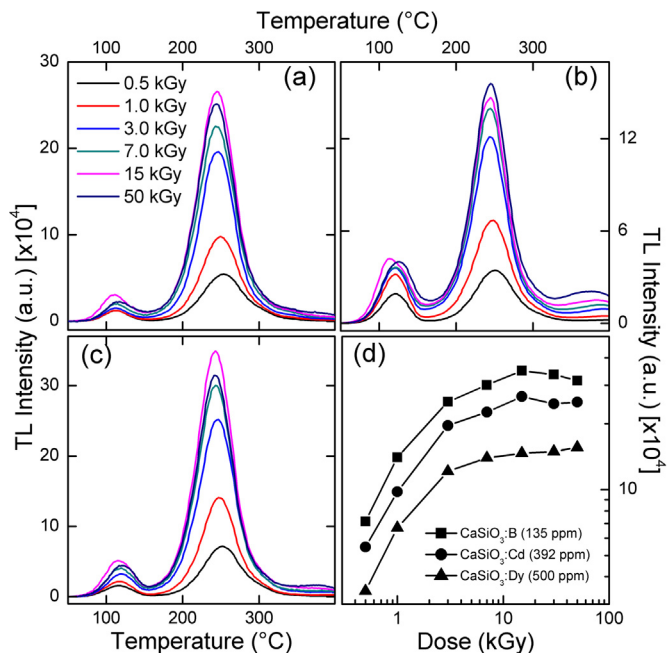


Fig. 8. TL glow curves of $\text{CaSiO}_3:\text{x}$ (a) $\text{x} = \text{Cd}$, (b) $\text{x} = \text{Dy}$ and (c) $\text{x} = \text{B}$ irradiated with gamma dose of 0.5–50 kGy. (d) TL intensity versus doses of the TL peaks at 270°C for three doped samples.


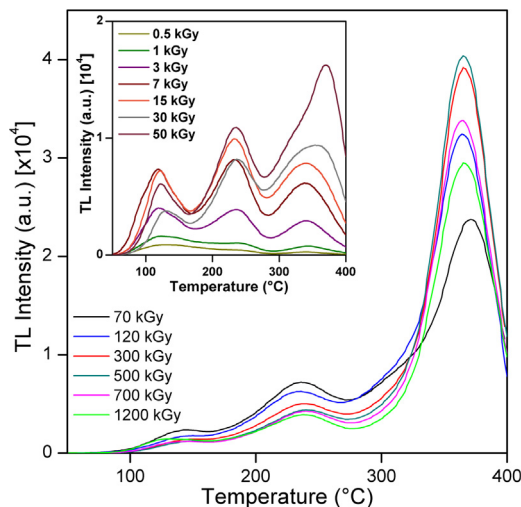


Fig. 9. TL glow curves of $\text{CaSiO}_3:\text{Eu}$ (1000 ppm) irradiated with gamma dose of 0.5–1200 kGy.

At this stage, we can only surmise following mechanism of TL emission:

- Ca substitutes for Si in SiO_4 tetrahedra. To compensate the charge disequilibrium, $[\text{CaO}_4]^{2-}$ attract either 2 monovalent cations or one divalent cation:



under irradiation 2M^+ will be liberated leaving a $(\text{CaO}_4/2\text{h})^-$ two holes center. During heating electrons liberated by oxygen vacancy that captured two electrons recombine with holes in $(\text{CaO}_4/2\text{h})^-$ and emit TL light.

- Rudra and Fowler [39] statement that in quartz, oxygen vacancies are formed in large concentration at room temperature and assumed that the same oxygen vacancies $(\text{VO})^{2+}$ are found also in silicate

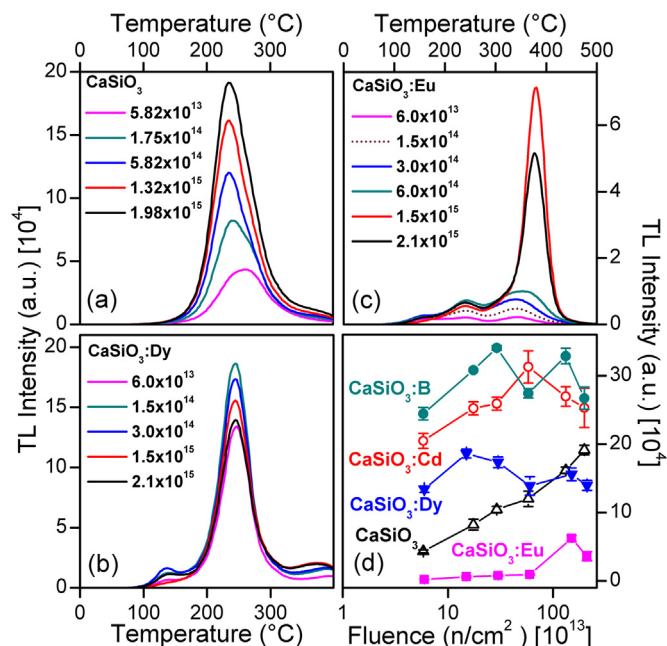


Fig. 10. Glow curve of (a) undoped CaSiO_3 , (b) $\text{CaSiO}_3:\text{Dy}$ and (c) $\text{CaSiO}_3:\text{Eu}$ irradiated with neutrons from research IEA-R1 with different fluencies. (d) TL intensity vs. neutron fluence for all samples.

minerals. When the crystal is irradiated with ionizing radiation large numbers of electron-hole are produced and oxygen vacancies capture each two-electrons: (VO, 2e). Toyoda and Ikeya [40] have shown that when the crystal is heated up to about 300 °C one electron from (VO, 2e) is liberated leaving E'_1 center. From 300 °C to about 450 °C the remaining electron is liberated.

Here, we assume that the irradiation produces non-bonding oxygen hole center (NBOHC) or (wet OHC) proposed by Ikeya [18]. During heating liberated electrons will recombine with hole in NBOHC and emit TL light.

At this moment, we cannot decide which one among (a) and (b) is the possible mechanism for TL emission. A work plan will be carried out in near future, for example, there is such Ca-hole-center, by EPR. Also by EPR we will find the concentration of NBOHC centers.

4. Conclusions

In this work CaSiO_3 polycrystals both pure and doped with B, Cd, Dy and Eu have been produced for electromagnetic radiation and thermal neutron detection. In the near future heavy ions dosimetry will be carry out. CaSiO_3 detectors are suited for that proposal.

CaSiO_3 (doped or not) is sensitive to low doses of the order of mGy, therefore it can be used in radiotherapy or nuclear medicine. Actually, we already have done application in nuclear medicine with good results. CaSiO_3 is also sensitive to high doses in the region of kGy, therefore it is a detector with wide range dosimetric capability.

One advantage of CaSiO_3 detectors is that although it has three TL peaks in the glow curve, the peak at about 250 °C is dominating, such that the two other peaks can be ignored.

Doped with B, Cd and Dy CaSiO_3 presented a similar behavior as the pure one, however, doping with Eu, the crystal presented a prominent third peak and weak first and second peak. One possibility, to be confirmed, is to Eu^{3+} substitute for silicon ion in $[\text{SiO}_4]$ and transforms into $[\text{Eu}^{3+}\text{O}_4/\text{h}]$ center, such that the main electron-hole recombination occur around 320–370 °C.

We are carrying out several EPR measurements under several radiation dose irradiation and under different annealing temperatures.

Under heavy irradiation we expect to identify the defects centers and the annealing procedures can establish connexion of these defects to TL peak temperatures.

The irradiation of CaSiO_3 with thermal neutrons the main effect is the (n, γ) reactions that takes place with Ca, Si and O. Therefore, the effect is that of irradiation of CaSiO_3 with γ -rays.

Acknowledgments

The authors wish to thank Ms. E. Somessari and Mr. C. Gaia, Institute for Energy and Nuclear Researches (IPEN), Brazil, for kindly carrying out the irradiation of the samples. To FAPESP (Process number 2014/03085-0) for partial financial support and to CNPq for fellowship to C.D. Gonzales-Lorenzo (Process number 162741/2015-4).

References

- [1] T. Nakajima, Y. Murayama, T. Matsuzawa, A. Koyano, Development of a new highly sensitive LiF thermoluminescence dosimeter and its applications, *Nucl. Instrum. Methods* 157 (1978) 155–162.
- [2] M.S. Akselrod, V.S. Kortov, D.J. Kravetsky, V.I. Gotlib, Highly sensitive thermoluminescent anion-defective $\alpha\text{-Al}_2\text{O}_3:\text{C}$ single crystal detectors, *Radiat. Prot. Dosim.* 32 (1990) 15–20.
- [3] A. Lakshmanan, A new high sensitive $\text{CaSO}_4:\text{Dy}$ thermostimulated luminescence phosphor, *Phys. Stat. Sol. (A)* 186 (2001) 153–166.
- [4] B. Obryk, M. Glaser, I. Mandi, P. Bilski, P. Olko, A. Sas-Bieniarz, Response of various types of lithium fluoride MCP detectors to high and ultra-high thermal neutron doses, *Radiat. Meas.* 46 (2011) 1882–1885.
- [5] B.N. Silva-Carrera, N.F. Cano, T.K. Gundu Rao, J.S. Ayala-Arenas, S. Watanabe, Thermoluminescence in Lapis Lazuli crystal: glow peaks and their connection with F-centers estimated by ESR analysis, *J. Lumin.* 188 (2017) 472–477.
- [6] T.K. Gundu Rao, N.F. Cano, B.N. Silva-Carrera, R.M. Ferreira, H.S. Javier-Callata, S. Watanabe, Centers responsible for the TL peaks of willemite mineral estimated by EPR analysis, *J. Lumin.* 177 (2016) 139–144.
- [7] N.F. Cano, L.H. Santos, J.F.D. Chubaci, S. Watanabe, Study of luminescence, color and paramagnetic centers properties of albite, *Spectrochim. Acta A* 137 (2015) 471–476.
- [8] S. Watanabe, N.F. Cano, L.S. Carmo, R.F. Barbosa, J.F.D. Chubaci, High- and very-high-dose dosimetry using silicate minerals, *Radiat. Meas.* 72 (2015) 66–69.
- [9] S. Watanabe, N.F. Cano, T.K. Gundu Rao, L.M. Oliveira, L.S. Carmo, J.F.D. Chubaci, Radiation dosimetry using decreasing TL intensity in a few variety of silicate crystals, *Appl. Radiat. Isot.* 105 (2015) 119–122.
- [10] R.F. Barbosa, N.F. Cano, S. Watanabe, R.A.S. Guttler, F. Reichmann, Thermoluminescence in two varieties of jadeite: irradiation effects and application to high dose dosimetry, *Radiat. Meas.* 71 (2014) 36–38.
- [11] N.F. Cano, A.R. Blak, J.S.A. Arenas, S. Watanabe, Mechanisms of TL for production of the 230 °C peak in natural sodalite, *J. Lumin.* 131 (2011) 165–168.
- [12] N.F. Cano, A.R. Blak, S. Watanabe, Electron paramagnetic resonance and the thermoluminescence emission mechanism of the 280 °C peak in natural andalusite crystal, *J. Lumin.* 131 (2011) 1545–1549.
- [13] N.F. Cano, A.R. Blak, S. Watanabe, Correlation between electron paramagnetic resonance and thermoluminescence in natural sodalite, *Phys. Chem. Miner.* 37 (2010) 57–64.
- [14] E.A. Gallegos, N.F. Cano, S. Watanabe, J.F.D. Chubaci, Thermoluminescence, infrared reflectivity and electron paramagnetic resonance properties of hemimorphite, *Radiat. Meas.* 44 (2009) 11–17.
- [15] N.F. Cano, J.M. Yauri, S. Watanabe, J.C.R. Mittani, A.R. Blak, Thermoluminescence of natural and synthetic diopside, *J. Lumin.* 128 (2008) 1185–1190.
- [16] N.F. Cano, J.M. Yauri, S. Watanabe, TL, EPR and optical absorption in natural grossular crystal, *J. Lumin.* 128 (2008) 1731–1737.
- [17] S.W.S. McKeever, M.S. Akselrod, Radiation dosimetry using pulsed optically stimulated luminescence of $\text{Al}_2\text{O}_3:\text{C}$, *Radiat. Prot. Dosim.* 84 (1999) 317–320.
- [18] M. Ikeya, *New Applications of Electron Spin Resonance*, World Scientific, Singapore, 1993.
- [19] J.R. Cameron, N. Suntharalingam, G.N. Kenney, *Thermoluminescent Dosimetry*, The University of Wisconsin Press, Madison, USA, 1968.
- [20] C.L. Wingate, E. Tochilin, N. Goldstein, Response of LiF to Neutrons and Charged Particles, in: *Proceedings of the Intern. Conf. on Luminescence Dosimetry*, University of Stanford, USA, 1967.
- [21] D.N. Souza, A.P. Melo, V.S.O. Gazano, L.V.E. Caldas, Characterization of Brazilian Wollastonite for radiation dosimetry, in: *Proceedings of the IJM, Acapulco, Mexico*, 2006.
- [22] C.B. Palan, K.A. Koparkar, N.S. Bajaj, S.K. Omanwar, Synthesis and TL/OSL properties of $\text{CaSiO}_3:\text{Ce}$ biomaterial, *Mater. Lett.* 175 (2016) 288–290.
- [23] W.A. Deer, R.A. Howie, J. Zussman, *An Introduction to the Rock-forming Minerals*, 2nd ed., Longman, England, 1992.
- [24] F.J. Trojer, The crystal structure of parawollastonite, *Z. Krist.* 127 (1968) 291–308.
- [25] T. Yamanaka, H. Mori, The structure and polytypes of $\alpha\text{-CaSiO}_3$ (pseudowollastonite), *Acta Cryst. B* 37 (1981) 1010–1017.
- [26] K.F. Hesse, Refinement of the crystal structure of wollastonite-2M

- (parawollastonite), Z. Krist. 168 (1984) 93–98.
- [27] H. Yang, C.T. Prewitt, On the crystal structure of pseudowollastonite (CaSiO_3), *Am. Mineral.* 84 (1999) 929–932.
- [28] D.N. Souza, A.P. Melo, L.V.E. Caldas, TL and TSEE response of Wollastonite-Teflon composites in X-ray beams, *Nucl. Instrum. Meth. A.* 580 (2007) 338–341.
- [29] D.N. Souza, A.P. Melo, M.G. Oliveira, L.V.E. Caldas, Dosimetric characterization of wollastonite-teflon composites, *Phys. Stat. Sol. C.* 4 (2007) 1175–1178.
- [30] S. Kulkarni, B.M. Nagabhushana, H. Nagabhushana, K.V.R. Murthy, C. Shivakumara, R. Damle, Synthesis, structural characterization and thermoluminescence properties of β -irradiated wollastonite nanophosphor, *Trans. Ind. Ceram. Soc.* 70 (2011) 163–166.
- [31] L. Hamidatou, H. Slamene, T. Akhal, B. Zouranen, Concepts, Instrumentation and Techniques of Neutron Activation Analysis, (2013), <http://dx.doi.org/10.5772/53686>.
- [32] J.R. Cameron, D.W. Zimmerman, TL vs R in LiF. A Proposed mathematical Model. Report. C00-1105-102, USAEC, 1965.
- [33] J.R. Cameron, D.W. Zimmerman, Modifications of the Mathematical Model. Report C00-1105-113, USAEC, 1966.
- [34] N. Suntharalingam, J.R. Cameron, Thermoluminescent response of lithium fluoride to radiations with different LET, *Phys. Med. Biol.* 14 (1969) 397–410.
- [35] E.W. Claffy, C.C. Klick, F.H. Attix, Proceedings of the the 2nd International Conference on Luminescent Dosimetry, Gatligberg, 1968.
- [36] E.F. Mische, S.W.S. McKeever, Mechanisms of supralinearity in lithium fluoride thermoluminescence dosimeters, *Radiat. Prot. Dosim.* 29 (1989) 159–175.
- [37] R. Chen, S.W.S. McKeever, Theory of Thermoluminescence and Related Phenomena, World Scientific Publication, Singapore, 1997.
- [38] S.W.S. McKeever, Thermoluminescence of Solids, Cambridge Uni. Press, Cambridge, 1985.
- [39] J.K. Rudra, W.B. Fowler, Oxygen vacancy and the E'_1 center in crystalline SiO_2 , *Phys. Rev. B* 35 (1987) 8223–8230.
- [40] S. Toyoda, M. Ikeya, Thermal stabilities of paramagnetic defect and impurity centers in quartz: basis for ESR dating of thermal history, *Geochem. J.* 25 (1991) 437–445.
- [41] T.M.B. Farias, S. Watanabe, A comparative study of the thermoluminescence properties of several varieties of Brazilian natural quartz, *J. Lumin.* 132 (2012) 2684–2692.