



issues	articles search
all issues	author search
current issue	subject search
table of contents	advanced search

português
español

Updated on
July 30, 2003

Materials Research
Revista Ibero-americana de Materiais

Print ISSN 1516-1439

- » [about the journal](#)
- » [editorial board](#)
- » [instructions to authors](#)
- » [subscription](#)
- » [statistics](#)

Publication of the
ABM, ABC, ABPol, SBCC, SBCr, SBMM, SBPMat

Mission

To publish original contributions on experimental, theoretical and simulation research on the processing, structure and properties of materials.

© 2003 Materials Research

Caixa Postal 676
13565-905 São Carlos SP - Brazil
Tel.: (55 16) 260-8527
Fax: (55 16) 261-5404

 Mail
dedz@power.ufscar.br



issues	articles search
prev/next	previous current next
author	subject
form	home

Materials Research
Print ISSN 1516-1439

Author selection	Search results	new search	contents	page bottom
------------------	----------------	------------	----------	-------------

Database : article

Search on : ALTAFIM, RUY ALBERTO CORREA [Author]

References found : 1 [refine]

Displaying: 1 .. 1 in format [ISO 690]

page 1 of 1

1 / 1

<input type="checkbox"/>	select
<input checked="" type="checkbox"/>	to print

Altafim, Ruy Alberto Corrêa, Murakami, Cacilda Ribeiro, Claro Neto, Salvador et al. **The effects of fillers on polyurethane resin-based electrical insulators.** *Mat. Res.*, June 2003, vol.6, no.2, p.187-191. ISSN 1516-1439
 · abstract in english · text in english

page 1 of 1

Author selection	Search top
------------------	------------

Refine the search

Database: article

Advanced form

Search for : Free form Basic form

	Search	in field	
1	ALTAFIM, RUY ALBERTO CORREA	Author	<input checked="" type="checkbox"/> index
2 and	<input checked="" type="checkbox"/>	All indexes	<input checked="" type="checkbox"/> index
3 and	<input checked="" type="checkbox"/>	All indexes	<input checked="" type="checkbox"/> index

Search engine: iAH powered by WWWISIS

BIREME/PAHO/WHO - Latin American and Caribbean Center on Health Sciences Information

The Effects of Fillers on Polyurethane Resin-based Electrical Insulators

Ruy Alberto Corrêa Altafim^{a*}, Cacilda Ribeiro Murakami^a, Salvador Claro Neto^b,
Luiz Carlos Ribeiro Araújo^b, Gilberto Orivaldo Chierice^b

^aDepartment of Electrical Engineering

^bSão Carlos Institute of Chemistry, São Carlos School of Engineering - University of São Paulo
C.P. 359, 13566-590 São Carlos - SP, Brazil

Received: November 29, 2000; Revised: December 8, 2002

The increasingly widespread use of polymeric insulators in vehicle distributors and transmission systems has led to an ongoing quest for quality and low costs. This quest has, in turn, resulted in improved performance and cost benefits, brought about by the use of new polymeric and composite resins. Occasionally, however, while some properties are improved, others may show a loss of optimal performance. Therefore, to understand the behavior of fillers, such as carbon black, silica and mica added to castor oil-derived polyurethane resins, several thermal, mechanical and electrical tests were conducted on samples and insulators produced specifically for this purpose, using these new materials. The results of these tests clearly demonstrated that this type of resin and its composites can be used to manufacture indoor electrical insulators and that the fillers analyzed in this study improve or maintain the characteristics of the pure resins.

Keywords: fillers, polyurethane resins, castor oil, and electric insulators


1. Introduction

Polymeric insulators are being used increasingly in distribution transmission electric systems, representing from 60 to 70% of newly installed HV insulators in North America¹. Non-ceramic composite insulator applications have expanded substantially owing to the advantages these insulators offer compared to the traditional ones of ceramic and glass. These advantages include light weight, higher mechanical strength to weight ratio, resistance to vandalism, superior performance in the presence of heavy pollution in wet conditions, and comparable or higher withstand voltage than porcelain or glass insulators. However, composite polymeric insulators also possess some disadvantages, such as superficial chemical changes caused by weathering and dry band arcing², erosion and tracking, which may ultimately lead to failure of the insulators³, difficult to evaluate service life, unknown reliability, and difficult to detect faulty insulators⁴. To minimize or eliminate some of these disadvantages, a wide range of materials and formulations have been tested in the production of polymeric insulators, among them bisphenol epoxy, cycloaliphatic epoxy resins, ethylene propylene rubber (EPR), silicone rubber (SIR), and cycloaliphatic epoxy. An ethylene propylene monomer

(EPM) and SIR alloy was introduced in 1986, but it was subsequently changed to an ethylene propylene diene monomer (EPDM) and SIR compound in 1989⁵.

A major obstacle for these technological advances and for research with these materials in Brazil is that all the basic components are imported and their characteristics may be modified at any time. Castor oil-based polyurethane resins, which are produced with 100% Brazilian technology and possess excellent electrical and mechanical characteristics, therefore play a crucial role, as reported in previous papers^{6,7}.

These resins consist of polymerized Urethane, which was first synthesized by Wurtz in 1849⁸ and is a product of the chemical reaction between an isocyanate group and a hydroxyl, or:

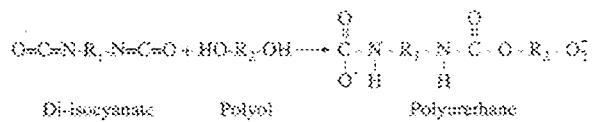

In this polymerization, a compound containing two or more isocyanate groups per molecule reacts with a polyol, or a polyfunctional alcohol⁸. Despite the apparent simplic-

*e-mail: altafim@sel.eesc.sc.usp.br

ity of this synthesis, any alterations in the polyol and pre-polymer ratio (-NCO/ -OH) cause substantial morphological changes in the resins' chains, leading to modifications in the material's mechanical properties, such as flexibility and rupture stress. The degree to which the polymer chains cross-link is controlled by the isocyanate group (-NHC_{OO}-) existing in the pre-polymer and by the hydroxyl group existing in the polyol. Any increase in this degree can cause an increase in the thermal energy required to reach the critical temperature for softening, called the glass transition temperature⁹. The castor oil used in the synthesis of these resins, which derives from the seeds of the tropical "castor-oil plant" (*Ricinus communis*), plays a crucial role, since it contains 81-96% of the triglyceride of 12-hydroxyoleic (or ricinoleic) acid, triricinolein. The high concentration of this triglyceride in castor oil makes it almost chemically pure, allowing it to be treated as a natural polyol⁹. Several resins containing this oil, that may have similar chemical compositions⁸ but considerably different physical properties, are available in the Brazilian market.

The research reported on here investigated two of these commercial resins, which were synthesized in mass proportions of 1:1 and 1:1.75 at the São Carlos Institute of Chemistry, University of São Paulo, Brazil and were labeled RI 1 and RI 2, respectively⁷. Both resins were subjected to a total curing time of approximately 24 h.

The resins' mechanical, electrical and thermal properties were improved by adding fillers such as carbon black, silica and mica to form composites. This study also analyzed electrical insulators made with these composites. Section 2 describes the experimental setup and the samples' compositions, while Sections 3 and 4 discuss the results of our investigation and our conclusions.

2. Experimental

2.1 Samples

Insulators and samples were produced by vacuum molding, using RI 1 and RI 2 resins doped with carbon black and silica having ~ 0.05 mm sized particles, and composites containing ~ 0.07 mm sized mica (cream colored) grains.

The carbon black and silica fillers, called C1, had a dual purpose: the former to provide protection against UV rays and the latter to reduce costs. The purpose of the mica filler, called C2, was to provide lamellar reinforcement and improve the material's dielectric, thermal and mechanical properties.

To facilitate the identification of the composites in this study, the names of the fillers were added to those of the resins; hence, the resins containing carbon black and silica were called RI 1C1 or RI 2C1, depending on the resin used (RI 1 or RI 2), while the resin containing mica was called RI 1C2 or RI 2C2.

2.2 Thermal tests

To determine the glass transition temperature, T_g, and the initial decomposition temperature, T_{id}, of the resins and their composites, thermal tests were carried out using equipment set up according to the technical DMA (Dynamic Mechanical Analysis) and TG (Thermal Gravimetry) requirements. RI 1C1 samples (resin, silica and carbon black with mass and weight proportions of 10:2:0.2, respectively) and RI 1C2 samples (resin and mica in the proportions of 10:1, 10:2, 10:3 and 10:4, respectively) were prepared for these tests. All the samples for these tests were prepared as 3 mm thick 60 × 12 mm rectangles.

The dynamic mechanical analysis was carried out using a DMA device (Du Pont Instruments, model 983) with a set frequency of 1 Hz, a three-point flexural mode, amplitude of 0.50 mm and a heating rate of 5 °C/min. The thermal gravimetry analysis was performed using a TA device (Du Pont Instruments, model 951), with a heating rate of 10 °C/min, nitrogen atmosphere, 50 ml/min flux and a 10 mg mass.

2.3 Mechanical tests

The mechanical tests to determine hardness, tensile strength and compressive strength were carried out on samples prepared according to the ASTM D229 standard¹⁰. Because preliminary results of the RI 2 resin and its composites showed an unfavorable thermal performance, only the RI 1C1 composites with a mass proportion of 10:2:0.2 and the RI 1C2 with mass proportions of 10:1; 10:2; 10:3 and 10:4 were subjected to mechanical tests.

The specimens were prepared in various shapes. For the hardness tests, the samples were 4.5 mm thick with 70 × 50 mm rectangular sections. For the tensile strength tests, performed at a speed of 5.08 mm/min, the samples had to conform to standardized type II specimens¹⁰. And for the compressive stress tests, performed at a speed of 1.30 mm/min, the samples were shaped into 12.7 mm diameter, 25.4 mm long cylinders.

2.4 Electrical tests

For the electrical tests, insulator samples were prepared from the RI 1 and RI 2 resins and its composites RI 1C1 and RI 2C1 with a mass proportion of 10:2:0.2 (resin, silica and carbon black, respectively) and, from the RI 1C2 and RI 2C2 with a mass proportion of 10:2 (resin and mica, respectively). Figure 1 shows one of the tested insulators. These tests were performed applying an increasing alternating voltage of 60 Hz at a uniform rate of 500 V/s on the insulator samples until its breakdown occurred. The alternating voltages were generated and measured using a High Voltage KIT (*Haefely Trench-100 kV*).

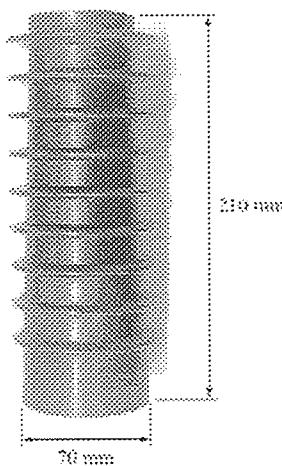


Figure 1. Insulator of the indoor type manufactured with polyurethane resin.

3. Results

3.1 Thermal tests

Tables 1 and 2 and Fig. 2a and 2b show the results of the thermal tests or the glass transition temperature, T_g and initial decomposition temperature, T_{id} . For the RI 2 resin and its RI 2C1 composite, the glass transition temperatures were not determined by filling the cell of the DMA apparatus with liquid nitrogen, because these temperatures were not part of the purpose of this study, which focused solely on polymeric insulators for use in tropical temperatures.

Figure 2 shows that, unfortunately, the variation of the proportion of mica added to the resins failed to influence the thermal characteristics. However, the T_g and T_{id} values of these composites with mica were found to be similar to those of pure resins. These results suggest that the use of these composites in manufactured products may substantially reduce their costs. Another important result was evidenced by the thermal tests performed with the DMA apparatus, which revealed alterations in the mechanical characteristics of the resins containing varied amounts of mica filler. These alterations consisted of an increase in the moduli of storage elasticity (E') values and a loss of (E'') values of these materials at an ambient temperature of 29.9 °C, as indicated in Table 2.

3.2 Mechanical tests

3.2.1 Hardness tests, Shore D scale

Table 3 shows the results of the hardness tests on the Shore D scale for rigid samples measured at five different points in each sample. As can be seen, the hardness of the

Table 1. Results of the thermal tests. Glass transition temperature, T_g and initial decomposition temperature, T_{id}

Type of Material	T_g (°C)	T_{id} (°C)
Resin RI 1 (10:0)	70.00	260.80
Resin RI 1C1 (10:2:0.2)	69.00	265.90
Resin RI 2 (10:0)	—	255.80
Resin RI 2C1 (10:2:0.2)	—	259.60
Resin RI 1 C2 (10:1)	71.00	257.10
Resin RI 1 C2 (10:2)	70.00	262.20
Resin RI 1 C2 (10:3)	69.00	262.00
Resin RI 1 C2 (10:4)	68.00	259.20

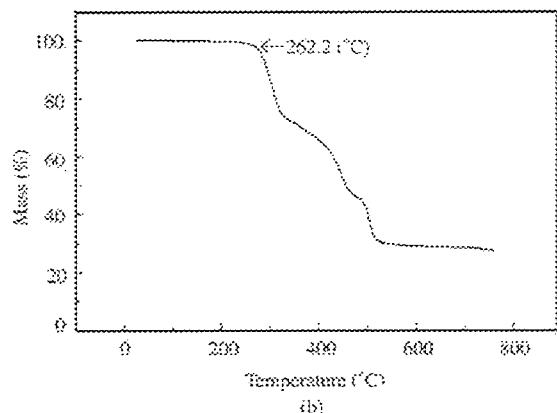
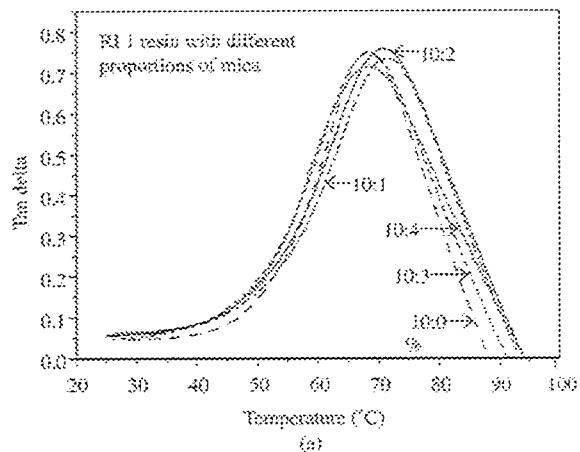


Figure 2. Curves of the characteristics: (a) T_g of the RI 1 resin with different proportions of mica filler; (b) T_{id} of the RI 1C2 resin with a mass proportion of 10:2.

RI 1 resin containing mica filler in varying mass proportions was very similar to that of the pure RI 1 resin. In contrast, however, the RI 2 resin and its RI 2C1 composite showed only half the hardness of the RI 1 resin.

Table 2. Variation of the E' and E'' moduli of the RI 1 resin with varying proportions of mica.

Mechanical characteristics	RI 1 (10:0) (without filter)	RI 1 C2 (10:1)	RI 1 C2 (10:2)	RI 1 C2 (10:3)	RI 1 C2 (10:4)
E' (GPa)	1.67	1.68	1.83	2.63	3.04
E'' (MPa)	78.45	99.29	111.20	140.50	162.10

Table 3. Hardness test results on the Shore D scale.

Type of Material	Hardness (Shore D)	Standard Deviation
Resin RI 1	79.40	0.55
Resin RI 1C1	80.80	0.45
Resin RI 1C2	79.40	0.55
Resin RI 2	45.00	0.71
Resin RI 2C1	48.00	0.55

Table 4. Tensile strength test results.

Type of Material	Tensile strength (MPa)	Standard Deviation
Resin RI 1	24.45	0.23
Resin RI 1C1	24.16	0.54
Resin RI 1C2	23.64	1.58
Resin RI 2	5.66	0.64
Resin RI 2C1	5.78	0.43

Table 5. Compressive strength test results.

Type of Material	Compressive strength (MPa)	Standard Deviation
Resin RI 1	193.23	34.32
Resin RI 1C1	257.87	51.04
Resin RI 1C2	279.98	39.40
Resin RI 2	90.61	12.82
Resin RI 2C1	90.07	3.91

Table 6. Voltage at which the polymeric insulators underwent external flashover.

Insulators manufactured from resins and composites	RMS Voltage of external flashover (kV)	Standard Deviation (RMS Voltage)
RI 1	84.78	0.25
RI 2	84.98	0.11
RI 1C1	83.65	0.36
RI 2C1	85.11	0.78
RI 1C2	84.58	0.11
RI 2C2	85.71	0.02

3.2.2 Tensile strength tests.

Table 4 shows that the RI 1 resin and its composites, RI 1C1 and RI 1C2, presented a higher tensile strength than the RI 2 resin and its composite RI 2C1 used in the production of insulators.

3.2.3 Compressive strength tests.

Table 5 lists the results of the compressive strength tests. The rupture compression strength values of the RI 1 resin and its RI 1C1 and RI 1C2 composites could not be measured with the apparatus available in our laboratory. However, the values given here are the peaks of compressive strength.

3.3 Electrical tests

Because the electric tests were performed on insulator samples and all the breakdowns occurred in the air rather than inside the polymeric insulator samples, the voltages listed in Table 6 are the withstand RMS voltages. The breakdown voltages of the polymeric insulators tested were higher than the ones shown here. According to Diesendorf¹¹, these voltages are not normally determined for non-restoring insulators.

4. Conclusions

The values of the glass transition temperature, T_g , and the initial decomposition temperature, T_{id} , listed in Table 1 allow us to conclude that the RI 2 resin and its composites RI 2C1 and RI 2C2 are potentially applicable in the manufacture of indoor products such as insulators. The RI 1 resin and its composites RI 1C1 and RI 1C2, on the other hand, can be used for both indoor and outdoor applications up to approximately 70 °C.

The silica and carbon black fillers added in these polyurethane resins did not significantly alter the thermal and mechanical properties of the composites compared to those of the pure resins, as shown in Tables 1, 3, 4 and 5. The mica filler, moreover, was found not to alter the composite's glass transition temperature.

The decomposition temperature, tensile strength, compressive strength and hardness values showed no sig-

nificant alterations, as illustrated in Tables 1, 3, 4 and 5 and Fig. 2. Table 2, however, reveals that the polymer's viscous elastic characteristics changed according to the mass proportion of mica, showing increased moduli of storage elasticity and loss. Further experimentation is therefore necessary to analyze the influence and importance of mica in electrical insulation applications.

With regard to the electrical tests, only the ultimate alternating voltage was determined because flashover occurred in the air and not inside the insulators. This RMS voltage presented values in excess of 80 kV, with a peak voltage above 113 kV. These values are extremely high for distribution line insulators, indicating that these resins and their composites have a good potential for such applications. However, further electrical tests should be performed, including impulse voltage tests.

Another benefit resulting from the use of mineral fillers, i.e., lower polymer insulator production costs, is shown in Table 6, which also demonstrates that the different fillers in the proportions used in this study did not interfere in the material's electrical behavior.

Acknowledgments

This study was made possible with the help and cooperation of the Institute of Chemistry of the University of São Paulo at São Carlos and the financial support of FAPESP, a Brazilian research funding institution.

References

1. Zhao, T.; Bernstorf, L. *Aging Tests of Polymeric Housing Materials for Non-Ceramic Insulators*, IEEE Electrical Insulations Magazine, v. 14, n. 2, p. 26-33, 1998.
2. Kim, S.H.; Cherney E.A.; Hacham, R.; Rutherford, K.G. *Chemical Changes at the Surface of RTV Silicone Rubber Coatings on Insulators During Dry Band Arcing*, IEEE Transactions DEI, v. 1, p. 106-123, 1994.
3. Gorur, R.S.; Cherney, E.A.; Hackam, R.; Orbeck, T. *The Electrical Performance of Polymeric Insulating Materials Under Accelerated Aging in Fog Chamber*, IEEE Transactions PD, v. 3, p. 1157-1164, 1988.
4. Kindersberg, J.; Scutz, A.; Karner, H.C.; Huir, R.V.D. *Service Performance, Material Design and Applications of Composite Insulators With Silicone Rubber Housings*, CIGRE 33-303, p. 1-5, 1996.
5. Hackam, R. *Outdoor HV Composite polymeric Insulators –Review*, IEEE Transactions on Dielectrics and Electrical Insulation, v. 6, n. 5, p. 557-585, October/1999.
6. Murakami, C.R.; Altafim, R.A.C.; Araújo, L.C.R.; Claro Neto, S.; Chierice, G.O., *Use of polyurethane resins derived from castor oil in the production of polymeric insulators – Part I*, 8th Regional Latin American Meeting - CIGRE, 15th Study Committee, Ciudad del Este, Paraguay, March/1999.
7. Altafim, R.A.C.; Murakami, C.R.; Araújo, L.C.R.; Claro Neto, S.; Chierice, G.O. *Polyurethane resins derived from castor oil for the fabrication of polymeric insulators – Part II*, 1999 Conference on Electrical Insulation and Dielectric Phenomena, IEEE Dielectrics and Electrical Insulation Society, Austin, Texas, October/1999.
8. Claro Neto, S. *Physical and chemical characterization of castor-oil derived polyurethanes used in bone implants*, Doctoral Thesis, São Carlos Institute of Chemistry, University of São Paulo, São Carlos, Brazil, 1997.
9. Araújo, L.C.R. *Chemical, thermal and mechanical characterization of polyurethane elastomers based on plant oil derivatives*, Dissertation for Master's degree, Institute of Chemistry of São Carlos, University of São Paulo, São Carlos, Brazil, 1992.
10. American Society for Testing and Materials, *ASTM D229 - Standard Test Method for Rigid Sheet and Plate Materials used in Electrical Insulation*, West Conshohocken, 1996.
11. Diesendorf, W. *Insulation Co-ordination in High Voltage Electric Power Systems*, Butterworth & Co. (Publishers) Ltd., London, 1974.